

Integration of peroxide delignification and sulfamic acid sulfation methods for obtaining cellulose sulfates from aspen wood

**Boris Kuznetsov^{1,2*}, Vladimir Levdansky¹, Svetlana Kuznetsova^{1,2},
Natalya Garyntseva¹, Irina Sudakova¹, Alexander Levdansky¹**

Abstract New method of cellulose sulfates obtaining from available and inexpensive raw material – aspen wood was developed. This method integrates catalytic peroxide delignification and sulfamic acid sulfation studies. Such solvents as acetic acid and water were used for isolation of pure cellulose by wood peroxide delignification with TiO₂ catalyst. Low-aggressive and less-toxic sulfating agent – sulfamic acid – urea mixture was used for obtaining of cellulose sulfates.

1 Introduction

Biologically active cellulose sulfates are used in perfumery, cosmetics, as sorbents materials and they have good prospects for application in medicine as antimicrobial, antiviral and anticoagulant agents (Zhang et al. 2015; Lin et al. 2012; Shibata 2011).

The most common raw material for obtaining of cellulose is the wood. At present the manufacture of cellulose from wood is an environmentally hazardous process because dangerous chemicals are involved in the wood delignification and pulp bleaching (Sixta 2006).

Catalytic delignification of wood in hydrogen peroxide- acetic acid - water medium at 120–130 °C allows producing the pure cellulose by one-step process without the use of ecology dangerous delignification and bleaching agents (Kuznetsov et al. 2008). But the different side reactions of low molecular mass products condensation with the formation of so-called “pseudo-lignin” (Hu et al. 2012) take place in wood peroxide delignification at elevated temperatures. The intensive mixing of a reaction medium and the fine grinding of wood were used to prevent the condensation reactions in aspen wood peroxide delignification with sulphuric acid catalyst (Kuznetsov et al. 2013). At these conditions the pure cellulose with a low content of residual lignin (less 1 %) was obtained from sawdust of aspen wood at temperature 100 °C and atmospheric pressure. The obtained cellulose is suitable for the production of different ethers, including cellulose sulfates.

Methods of cellulose sulfates obtaining commonly use such sulfating agents, as H₂SO₄, (Chen et al. 2013) SO₃, (Qin et al. 2014) ClSO₃H (chlorosulfonic acid) with solvents Py, DMF, DMSO (Zhu et al. 2014), 1,4-dioxane, (Kuznetsov et al. 2015) ionic liquids (Wang et al. 2009) and others. The most effective sulfating agents are complexes of SO₃ with organic bases such as tertiary amines, Py, DMF, etc. However, SO₃, H₂SO₄, and ClSO₃H are rather aggressive and toxic reagents.

* Corresponding author. Tel.: +7 391 249 48 94. Fax: +7 391 205 19 42. E-mail: bnk@icct.ru; inm@icct.ru (B.N. Kuznetsov)

¹ Institute of Chemistry and Chemical Technology SB RAS; Federal Research Center “Krasnoyarsk Science Center SB RAS” Akademgorodok, 50-24, Krasnoyarsk, 660036, Russia

² Siberian Federal University, Svobodnyi, 79, Krasnoyarsk 660041, Russia

Less dangerous sulfating agent is the sulfamic acid, which produced in industry by the reaction of urea with H_2SO_4 . The use of sulfamic acid for cellulose sulfation in an N_2O_4 – DMF system was reported (Wagenknecht et al. 1993). But the degree of substitution of cellulose sulfates obtained by this method was less than 0.4 under the conditions employed.

The direct sulfation of cellulose with $\text{NH}_2\text{SO}_3\text{H}$ in DMF was described (Zhang et al. 2011). In comparison with chlorosulfonic acid, the sulfamic acid reacts with cellulose only at elevated temperature (70–80 °C). Obtained cellulose sulfates were soluble in water and had degree of substitution 1.78–1.89. The main disadvantage of this method is a quite long reaction time (up to 24 h.). In paper (Huang and Zhang 2010) the reaction of cotton cellulose with $\text{NH}_2\text{SO}_3\text{H}$ was carried out in a laboratory oven at high temperature which promoted the partial destruction of sulfated products.

The results of the study of new method of cellulose sulfates obtaining from aspen wood, which integrates the stages of pure cellulose isolation by wood peroxide delignification with TiO_2 catalyst and further sulfation of cellulose by sulfamic acid–urea mixture are described in the present paper. In contrast to previously studied method of aspen wood oxidative delignification with H_2SO_4 catalyst (Kuznetsov et al. 2013) the non-toxic and non-corrosive TiO_2 catalyst is used for pure cellulose isolation from aspen wood under mild conditions (100 °C, 0.1 MPa). The less-aggressive and less-toxic sulfating agent – sulfamic acid–urea mixture is employed for cellulose sulfation instead of dangerous traditional sulfating agents (e.g. chlorosulfonic acid–pyridine mixture).

2 Materials and methods

2.1 Cellulose obtaining from aspen wood

Air dry sawdust (fraction 2–5 mm) of aspen wood (*Populus tremula* L.) harvested in the forest area near Krasnoyarsk city was used as initial raw material. The chemical composition of aspen wood (% on abs. dry wood) is 46.5 cellulose, 21.7 lignin, 23.5 hemicelluloses, 0.43 mineral part.

Cellulose was isolated from aspen wood using the original method of oxidative delignification by H_2O_2 with TiO_2 catalyst under the mild conditions. Commercial TiO_2 (GOST 9808-84) with an average particle size near 10 μm , phase composition: rutil 92 %, anatase 8 %, BET surface area 3 m^2/g was used as a catalyst.

Delignification of wood sawdust was carried out in a glass reactor of 250 cm^3 volume supplied by mechanical stirrer, condenser and thermometer. Aspen wood sawdust (10 g) was placed to the reactor and a mixture of acetic acid, hydrogen peroxide, distilled water and TiO_2 was added. The reaction mixture was heated up to the required temperature and was vigorously stirred (700 rpm) during 1 – 4 h. After that the reaction mixture was cooled and the obtained cellulosic product was separated under vacuum using Buchner funnel, following washing by distilled water and drying at 105°C until constant weight.

Cellulosic product yield was estimated by gravimetric method and calculated as follows: $\text{yield} = (m/m_0 \times 100 \%)$, where m is the mass of abs. dry cellulosic product (g), m_0 is the mass of abs. dry wood (g).

Three replicates were used for each case and average yields of cellulose were calculated. The deviations are given for experimental data in Tables 1 and 2.

2.2 Sulfation of cellulose with sulfamic acid–urea mixture

Cellulose (1.62 g), urea (1.80 g), sulfamic acid (3.40 g) and diglyme or DMF (40 ml) were placed in a three necked flask (100 ml) equipped with stirrer, thermometer and reflux. The mixture was boiled under reflux at vigorous stirring within 1–4 hours. After that, the mixture was cooled to 15–20 °C, poured into 50 ml of 75 % water-ethanol solution containing 3–4 % sodium hydroxide and stirred. The resulting sodium salt of cellulose sulfate was separated by filtration, washed with 96 % ethanol, and dried under vacuum. The obtained product was then dissolved in 50–60 ml distilled water, filtered and dialyzed on cellophane against distilled water. After dialysis the aqueous solution of sodium salt of cellulose sulfate (NaCS) was concentrated under vacuum until complete removal of water.

The yield of NaCS (Y) was calculated according to the Eq. 1:

$$Y = \text{mol (NaCS)} / \text{mol (Cell)} \times 100 \% \quad (1)$$

where mol (NaCS) – is the mol of NaCS (g) and mol (Cell) – is the mol of initial cellulose.

Three replicates were used in each case and average yields of NaCS were calculated. The deviations are given for experimental data throughout the text.

2.3 Characterization methods

Elemental analysis (C, H, N, S, O) was performed with the use of Flash EATM 1112 analyzer (Thermo Quest, Italy).

The degree of substitution (DS_S) of cellulose sulfates was calculated according to the Eq.2 (Gericke et al. 2009):

$$\text{DS}_S = (162.1 \times W_S) / (3207 - 102.1 \times W_S) \quad (2)$$

where W_S – is the sulfur content (%).

The contents of cellulose, lignin and hemicelluloses in solid products were defined by analytical methods, common in wood chemistry (Sjöström and Alen 1999).

The content of cellulose was determined gravimetrically according to Kürschner and Hoffer. A portion of 1 g cellulosic product was weighed into an Erlenmeyer flask. 25 mL of a mixture of nitric acid in ethanol (1:4, v/v) was added followed by one-hour boiling under reflux. The solid was separated from the solution using a glass filter (40 µm). This procedure was repeated twice and a third time with hot water for 30 min. The glass filter was then dried at 105 °C and weighed.

For the gravimetric determination of holocellulose 0.3 g of cellulosic product was dispersed in 45 mL water and 60 µL glacial acetic acid and 0.3 g sodium chlorite were added. The mixture was kept at 75 °C in a shaking device for 5 h. Acetic acid and sodium chlorite were added after every hour. Afterwards the holocellulose was separated by filtration using a glass filter (40 µm), washed and dried at 105 °C and weighed (Rossberg et. al. 2014).

The content of hemicelluloses was calculated as the difference in weights of holocellulose and cellulose.

Acid-insoluble lignin (Klason lignin) was determined according the following procedure. 1 g of cellulosic product was placed in 100-mL beaker and then added 15.0 mL of 72 % sulfuric acid. The acid was added gradually in small increments while stirring and macerating the material with a glass rod. After the specimen was dispersed, the beaker was covered with a watch glass and kept it in a bath at 20 °C for 2 h. The material was stirred frequently during this time to ensure complete solution. Then the material was transferred from the beaker to the flask and 300 mL of water was added to a flask to dilute solution to 3 % concentration of sulfuric acid. The solution was boiled for 4 h, maintaining constant volume by using a reflux condenser. Then the lignin was transferred quantitatively on the filter, using hot water, washed and dried in an oven at 105.3 °C to constant weight (TAPPI 1998).

The lignin content was calculated in the test specimen as follows:

$$\text{Lignin, \%} = A \cdot 100 / W$$

where: A = weight of lignin, g

W = oven-dry weight of test specimen, g

Intrinsic viscosity of cellulose was measured and degree of polymerization was calculated according to ASTM 1795-13. 0,25 g. of dry cellulose was placed in 100 ml glass flask that can be tightly closed by screw cap. 25 ml of distilled water was added to the flask and shook in order to disperse the cellulose sample. The air from the flask was swept out with a stream of nitrogen. 25 ml of cupriethylenediamine was added, the cap was inserted tightly and the solution was shaken in a mechanical shaker bath at 20 °C until the cellulose completely dissolved. Then 10 ml of the

cellulose solution was transferred by pipette to a viscometer (VPG -3) previously placed in the temperature control bath at 20 °C. The solution was left for at least 5 min to reach bath temperature. By applying suction, the solution into the lower line of the viscometer was drawn until top meniscus. The efflux time, the time required for the meniscus to pass from upper mark to the mark below, was measured at least three times. The outflow time of solvent was determined in the same condition.

The Mark-Houwink equation was used for the calculation of average degree of polymerization (Wang et al. 2016, Oberlerchner et al. 2015)

$$[\eta] = K \cdot M_r^\alpha$$

All experiments were performed in triplicate and average values reported. Experimental errors, which were calculated as the relative standard deviation, are shown in text and in the tables.

FTIR analysis was carried out in transmission mode using the Tensor 27 spectrometer (Bruker, Germany). Samples of products (3 mg for each) were prepared in pellet with matrix KBr. The spectra were recorded in range 400–4000 cm^{-1} wavelength. Spectral data were processed by program OPUS/YR (version 5.0).

FT Raman spectra of the samples were recorded using Bruker RFS 100/S spectrometer with a liquid-nitrogen cooled Ge diode as detector over a range of 3500-100 cm^{-1} . A cw-Nd:YAG-laser with an exciting line of 1064 nm was applied as light source for the excitation of Raman scattering. The analysis of the data was executed with OriginPro 7.0 (OriginLab Corp. MA USA).

X-ray diffraction analysis was carried out on PANalytical X'Pert Pro diffractometer using Cu-K α source ($\lambda = 0.154$ nm) in the 2θ range 5–70 ° and scanning step width of 0.01 °/scan.

Crystallinity index (CI) was calculated from the ratio of the height between the intensity of the crystalline peak ($I_{002} - I_{AM}$) and total intensity (I_{002}) after subtraction of the background (Park et al. 2010).

^{13}C NMR spectra were recorded at temperature 25 °C with spectrometer Bruker Avance III 600 MHz. The samples were dissolved in D_2O .

The electron images were obtained with scanning electron microscope TM-1000 HITACHI (Japan) with accelerating potential 15 kV. Samples were coated on carbon support.

3 Results and discussion

The developed method of cellulose sulfates obtaining from aspen-wood includes the steps of cellulose isolation by wood peroxide delignification in acetic acid-water medium in the presence of suspended TiO_2 catalyst and the sulfation of obtained cellulose by sulfamic acid-urea mixture in diglyme or DMF (Fig. 1):

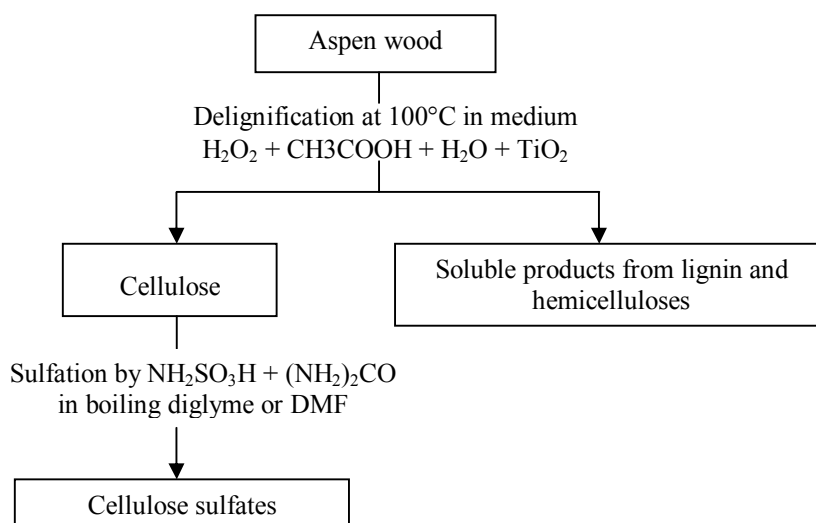


Fig. 1 Scheme of cellulose sulfates obtaining from aspen wood

3.1 Peroxide delignification of aspen wood with TiO₂ catalyst

In the present study the regularities of aspen wood delignification in the medium “hydrogen peroxide – acetic acid – water” was first studied in the presence of solid TiO₂ catalyst under mild conditions (temperatures 70–100 °C, atmospheric pressure).

The influence of temperature, concentrations of hydrogen peroxide and acetic acid on the dynamics of lignin removal from wood was studied at fixed liquid/wood ratio (LWR) equal to 15.

The increase of temperature and time of delignification process significantly reduces the content of residual lignin in the cellulosic product (Fig. 2). But at the same time the yield of cellulosic product is decreased (Table 1).

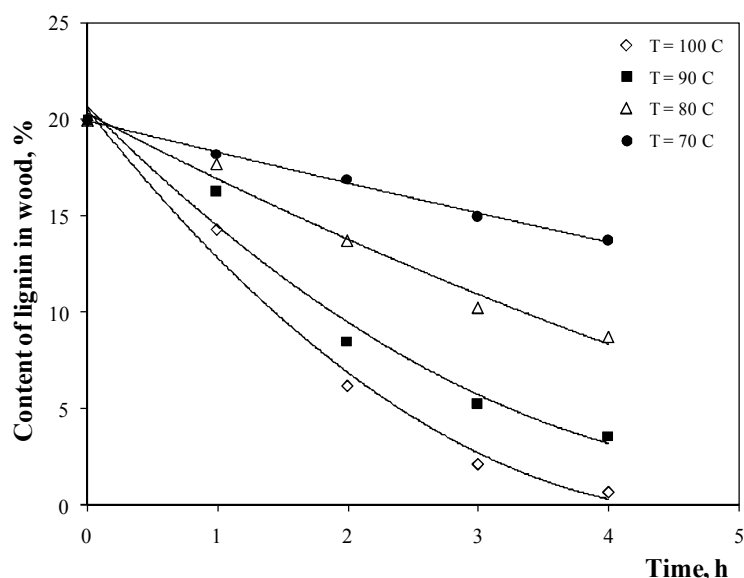


Fig.2 Dynamics of lignin removal from aspen wood in the presence of 1 % TiO₂ catalyst at concentration of H₂O₂ 5 %, CH₃COOH 25 % and LWR 15

Table 1 Influence of delignification time on the yield and composition of cellulosic product

Delignification conditions: 100 °C, H₂O₂ – 5 %, CH₃COOH – 25 %, LWR 15. Data represent percentages of oven dry weight (odw) (mean ± SD)

Time, h	Yield of cellulosic product, %*	Composition of product, % **		
		cellulose	hemicelluloses	lignin
2	72.5 ± 1.8	85.8 ± 1.9	7.8 ± 0.2	6.1 ± 0.2
3	62.5 ± 1.6	90.4 ± 2.0	7.2 ± 0.2	2.1 ± 0.1
4	50.2 ± 1.2	93.5 ± 2.1	5.5 ± 0.1	0.7 ± 0.1

*to the abs. dry wood ** to the abs. dry cellulosic product

The cellulosic product obtained from aspen wood at temperature 100°C and time of delignification 4 h has the lowest content of residual lignin (0,7 %). These fixed temperature and time were used for study the impact of H₂O₂ and CH₃COOH concentrations on the yield and composition of cellulosic product (Table 2).

Table 2 Influence of concentration of H₂O₂ and CH₃COOH on the yield and composition of cellulosic product obtained from aspen wood at 100°C and time 4h. Data represent percentages of oven dry weight (odw) (mean ± SD)

	H ₂ O ₂ , %*				CH ₃ COOH, %**		
	3	4	5	6	15	25	35
Yield, %	65.9 ± 1.7	50.8 ± 1.3	50.2 ± 1.2	49.8 ± 1.2	67.4 ± 1.6	50.2 ± 1.2	50.4 ± 1.3
Composition, %:							
cellulose	85.7 ± 2.1	91.8 ± 2.3	93.5 ± 2.1	94.2 ± 2.3	84.4 ± 1.9	93.5 ± 2.1	92.0 ± 2.3
hemicelluloses	7.8 ± 0.2	6.3 ± 0.2	5.5 ± 0.1	5.3 ± 0.1	9.2 ± 0.2	5.5 ± 0.1	6.3 ± 0.2
lignin	6.2 ± 0.2	1.6 ± 0.1	0.7 ± 0.1	0.2 ± 0.1	6.1 ± 0.2	0.7 ± 0.1	0.2 ± 0.1

*at CH₃COOH concentration 25 %; **at H₂O₂ concentration 5 %

It was found, that the concentrations of H₂O₂ and acetic acid impact significantly on the content of residual lignin in cellulosic product. The increase of H₂O₂ concentration from 3 to 5 % reduces the content of lignin in cellulose from 6.2 up to 0.7 %.

According to XRD data (Fig. 3), the unit cell of cellulosic product obtained from aspen wood is identical to the monoclinic unit cell of cellulose I (Nishiyama 2002). The crystallinity index of aspen cellulose (0.70) is a little less than that of the commercial microcrystalline cellulose (MCC) Vivapur 101 (0.75) (Park et al. 2010).

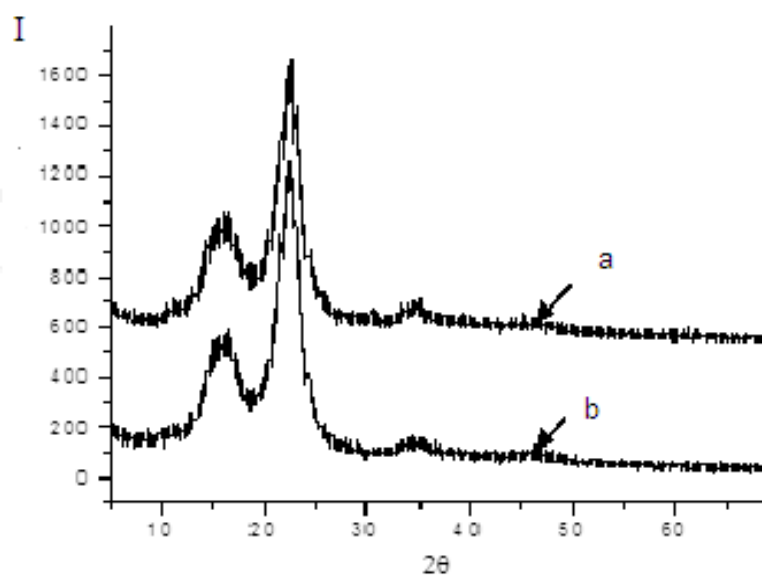


Fig. 3 XRD patterns of aspen wood cellulose (a) and of commercial MCC Vivapur 101 (b)

The similarity of FTIR spectra of cellulosic product from aspen wood and of industrial MCC Vivapur 101 (Fig. 4) indicates a similar composition of the both samples. In accordance with literature data (Fengel 1992) the broad absorption band in the region 3400–3500 cm⁻¹ is due to vibration of hydrogen-bonding –OH groups and the absorption peak at 2900 cm⁻¹ belongs to CH₂ groups. The absorption peaks at 1164 cm⁻¹ and at 896 cm⁻¹ belong to vibrations of C–O–C and C–H bonds, accordingly.

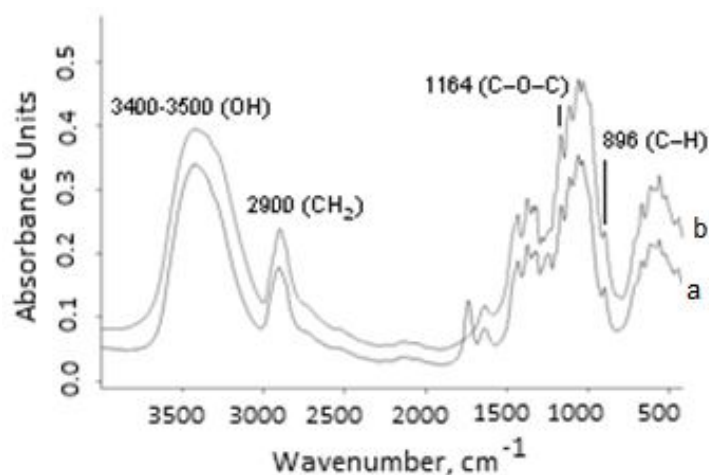


Fig. 4 FTIR spectra of cellulose obtained from aspen wood (a) and of MCC Vivapur 101(b)

The absence of peaks located in the range 1509–1609 cm^{-1} , which correspond to vibrations of aromatic ring confirms the complete removal of lignin from cellulosic product. The absorption peak which corresponds to either the acetyl or uronic ester groups of hemicelluloses normally appears in the region 1700–1740 cm^{-1} . The presence of absorption peak at 1735 cm^{-1} in spectrum of aspen cellulose indicates the presence of hemicelluloses in the sample.

According to SEM data the samples of cellulose from aspen wood and industrial MCC consist of microfibrils with different length (Fig. 5). Some of microfibrils are collected the bundles.

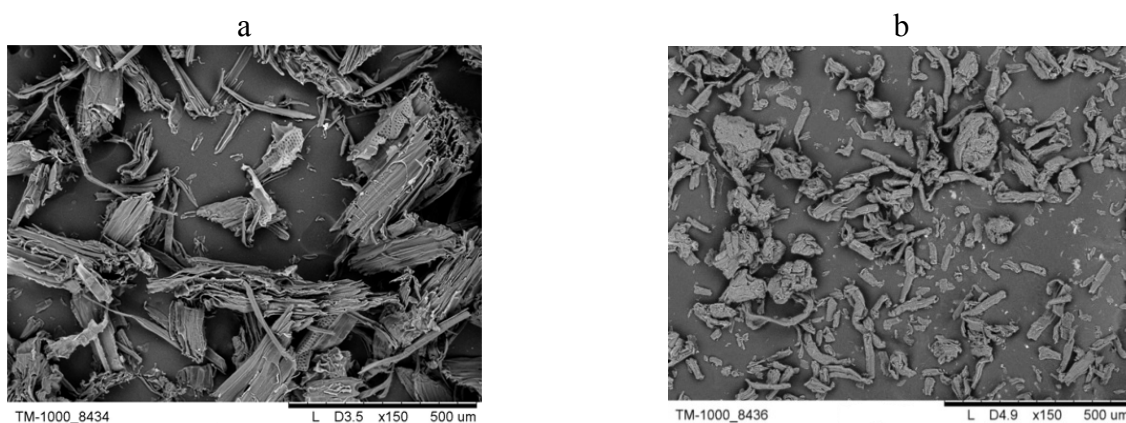


Fig.5 SEM images of cellulose, obtained from aspen wood with TiO_2 catalyst (a) and of commercial MCC Vivapur 101 (b) at magnification 1000 times

As a result of the accomplished study the green method of aspen-wood peroxide delignification under the mild conditions in the medium of “ H_2O_2 - CH_3COOH - H_2O - TiO_2 catalyst” was developed.

The regularities of aspen-wood peroxide delignification in acetic acid–water medium at 70–100 °C in the presence of 1 % TiO_2 catalyst are the same as for catalyst 2 % H_2SO_4 (Kuznetsov et al. 2011). For both catalysts the increase of H_2O_2 and CH_3COOH concentrations in the reaction mixture and time of the process reduced the content of residual lignin in cellulose product and decreased the yield of product. The peroxide delignification processes are described satisfactory by the first order equations for both of TiO_2 and H_2SO_4 catalysts. But in contrast to H_2SO_4 catalyst, the TiO_2 catalyst is non-toxic and corrosively non-active material. The more technologically convenient TiO_2 catalyst at first was used for preparation of pure microcrystalline cellulose from aspen wood at mild conditions.

The cellulosic product containing 93.5 % of cellulose, 5.5 % of hemicelluloses 0.7 % of lignin was isolated from aspen wood with the yield 50.2 % at the next conditions of delignification process: temperature 100 °C, concentrations


of H₂O₂ 5 %, CH₃COOH 25 %, TiO₂ 1 %, LWR 15, time 4 h. This product has the degree of polymerization 450±10 and crystallinity index 0.70, just like the commercial MCC.

The obtained cellulosic product was used for synthesis of cellulose sulfates.


3.2 Sulfation of cellulose from aspen wood by sulfamic acid – urea mixture

Chlorosulfonic acid (ClSO₃H) is the common reagent for sulfation of cellulose (Zhu et al. 2014; Wang et al. 2007). In order to prevent the destruction reactions the sulfation of cellulose by chlorosulfonic acid is usually carried out below 30°C. This makes possible to obtain cellulose sulfates with high degree of substitution (up to 1.70).

Since, ClSO₃H is a corrosive, high toxic reagent, the less-toxic sulfamic acid is the best alternative. In this study the urea was used as a catalyst to improve the reactivity of NH₂SO₃H in the sulfation of cellulose from aspen wood. The higher activity of sulfamic acid – urea mixture in sulfation of polysaccharides (Al-Horani and Desai 2010) is explained by the formation of donor-acceptor complex:

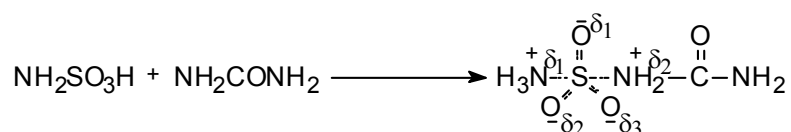

Cellulose sulfates, obtained with the use of sulfamic acid–urea mixture were isolated in the form of ammonium, sodium, and potassium salts according to scheme:

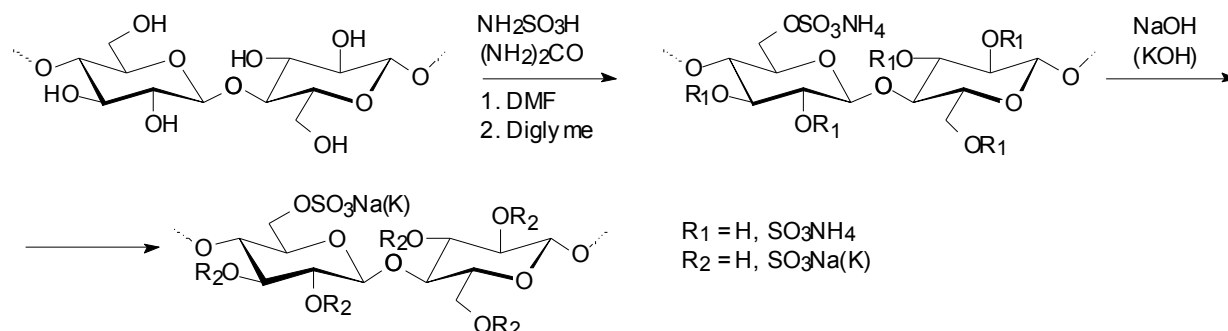

The reaction of cellulose sulfation by sulfamic acid - urea mixture in DMF or diglyme proceeds in a heterogeneous medium. Fig. 6 illustrates the variation of yield and sulfur content in cellulose sulfates with time of cellulose treatment by sulfamic acid–urea mixture.

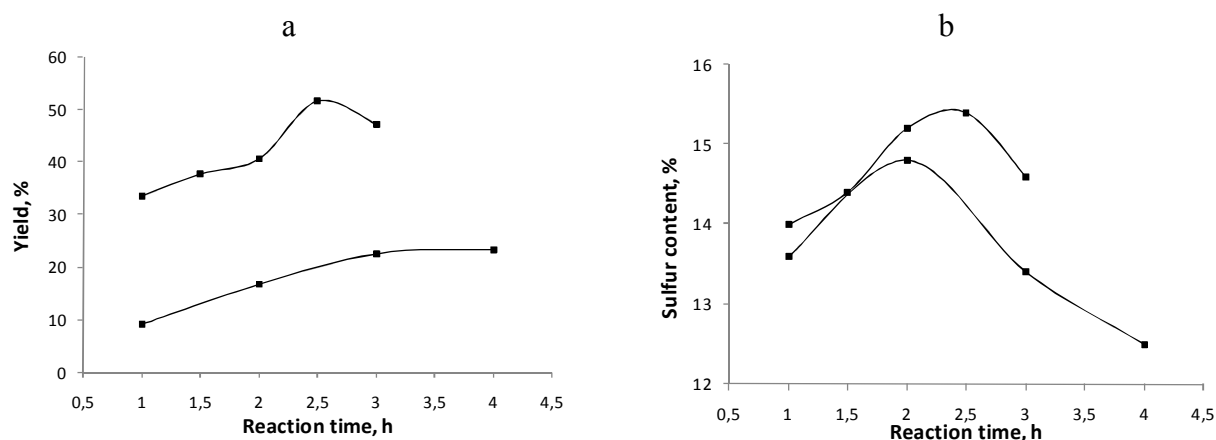


Fig. 6 Variation of yield (a) and sulfur content (b) in cellulose sulfates from aspen wood with time of cellulose treatment by sulfamic acid–urea mixture in diglyme (1) and in DMF (2)

The rather high sulfur content in the cellulose sulfates obtained in diglyme ($14.0\pm 0.3\%$) and in DMF ($13.6\pm 0.3\%$) was observed at the reaction time 1 h. At the reaction time 2–2.5 h the maximal sulphur content in cellulose sulfates reaches $15.2\pm 0.4\%$ in diglyme (after 2.5 h) and $14.8\pm 0.3\%$ in DMF (after 2 h). These values correspond to the degree of substitution 1.5 and 1.4, respectively. The further increase of the reaction time reduces the sulphur content in cellulose sulfates. The maximal yield of cellulose sulphate ($51.6\pm 0.6\%$) was obtained in the presence of diglyme after sulfation during 2.5 h. This sample contains $15.4\pm 0.4\%$ of sulphur and it has the degree of substitution 1.53.

The sulfation of cellulose in boiling diglyme at $161\text{ }^{\circ}\text{C}$ results in less cellulose degradation than that in boiling DMF at $152\text{ }^{\circ}\text{C}$. Besides, the use of diglyme as a solvent increases the yield of cellulose sulfate by 2.5 times as compared to DMF.

According to XRD data the disordering of cellulose crystalline structure takes place during sulfation process.

FTIR and Raman spectra of cellulose sulfates (Fig. 7, 8) contain the absorption peaks corresponding to vibrations of C–O–S and O=S=O bonds (Wang et al. 2007; Zhang et al. 2010). This confirms the presence of sulfate groups in the structure of cellulose.

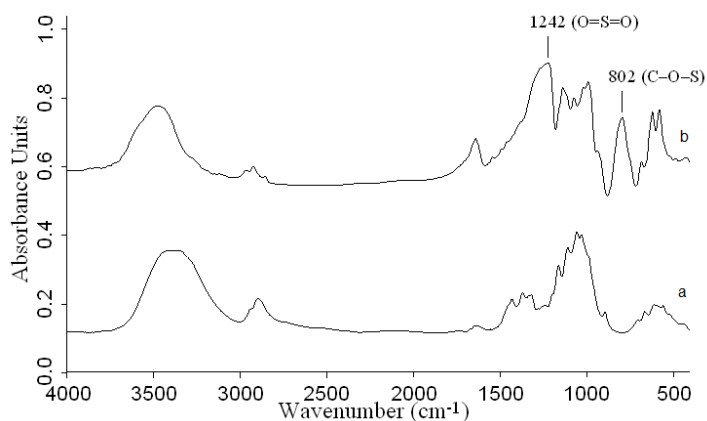


Fig. 7 FTIR spectra of initial cellulose from aspen wood (a) and of sodium salts of cellulose sulfate (b) obtained by sulfation of cellulose with sulfamic acid–urea mixture in diglyme (sulfur content $15.4\pm 0.4\%$)


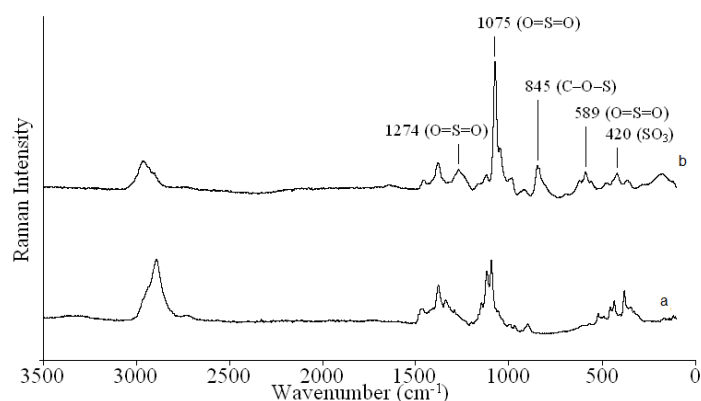


Fig. 8 Raman spectra of initial cellulose from aspen wood (a) and of sodium salts of cellulose sulfate (b) obtained by sulfation of cellulose with sulfamic acid–urea mixture in diglyme (sulfur content $15.4\pm 0.4\%$)

It is known (Wang et al. 2007), that the hydroxyl group at C6 primary carbon atom is predominantly sulfated in a glucopyranose unit of cellulose:



The hydroxyl group connected with carbon atom C2 is less reactive in the sulfation process. The hydroxyl group at C3 carbon atom is replaced on sulfate groups only under hard sulfation conditions, which promote the destruction of cellulose.

For cellulose sulfates the chemical shifts in ^{13}C NMR spectra corresponding to carbon atoms C1 – C6 in glucopyranose units of cellulose are observed at 102 (C1), 74 (C2), 73 (C3), 79 (C4), 77 (C5) and 60 (C6) ppm (Wang et al. 2007). The introduction of sulfate groups into cellulose moves the chemical shifts of carbon atoms to lower magnetic field (Table 3).

Table 3 Chemical shifts of carbon atoms in ^{13}C NMR spectra of cellulose and cellulose sulphates samples obtained from aspen wood

Sample	Chemical shift, p.p.m.					
	C1	C2	C3	C4	C5	C6
Cellulose	102.0	74.1	73.8	79.5	77.4	60.1
Sodium salt of cellulose sulfate obtained with the use of $\text{NH}_2\text{SO}_3\text{H}$ – urea mixture in DMF	100.3	74.5	72.8	78.9	77.5	–
Sodium salt of cellulose sulfate obtained with the use of $\text{NH}_2\text{SO}_3\text{H}$ – urea mixture in diglyme	100.6	74.6	72.8	78.7	77.6	–

In ^{13}C NMR spectra of the obtained cellulose sulfates (Fig. 9) the signal of carbon atom C6 moves completely from 60 to 66 ppm. It means that all hydroxyl groups connected with carbon atoms C6 are substituted in cellulose sulfates on sulfate groups. Appearance of a new signal at 80–82 ppm indicates that only a part of OH-groups, connected with C2 atoms is substituted on sulfate groups in cellulose sulfates. No shift of a signal of C3 atom was observed, that indicates the absence of sulfate group at C3 atoms in cellulose sulfates.

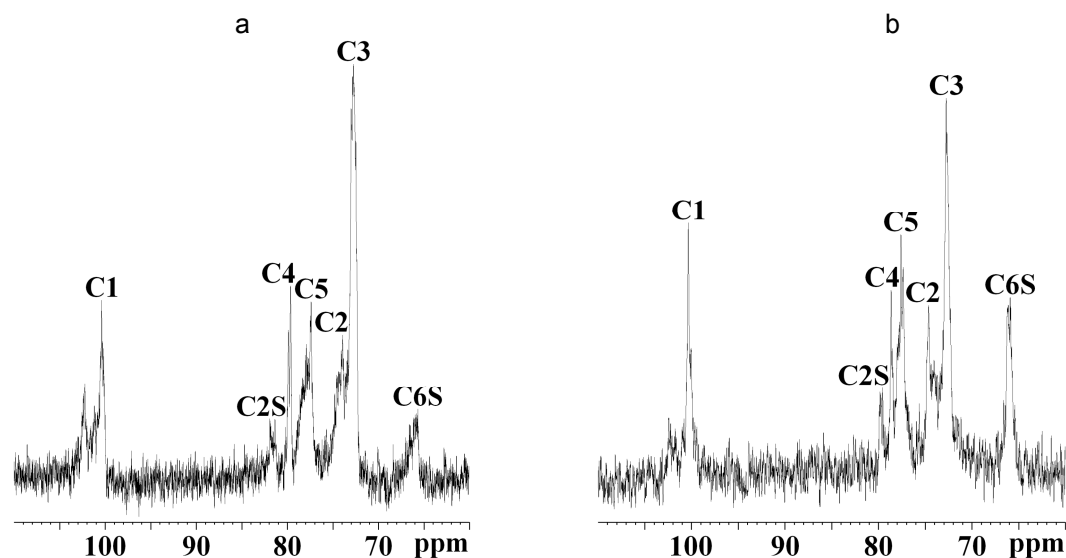


Fig. 9 ^{13}C NMR spectra of sodium salts of cellulose sulfates obtained by sulfation of cellulose with sulfamic acid–urea mixture in DMF (a) and in diglyme (b) (sulfur content 14.8 ± 0.3 and 15.2 ± 0.4 % respectively)

The similar results were reported early for cellulose sulphates obtained with the use of another sulphating agents: H₂SO₄ (Chen et al. 2013), SO₃ (Qin et al. 2014), chlorosulfonic acid (Kuznetsov et al. 2015, Zhu et al. 2014).

For the process of cellulose sulfation by different sulphating agents in the medium N₂O–DMF it was established that the sulphating activity increased in the range: H₂SO₄ << NH₂SO₃ ~ NOSO₄H < SO₂ < ClSO₃H < SO₃ < SO₂Cl₂ (Wagenknecht et al. 1993).

The regiospecificity is an important characteristic of cellulose sulfates that defines their properties. It is known from the literature that in obtaining cellulose sulfates by different sulfation methods the hydroxyl group at C6 carbon atom is predominantly sulfated while OH-groups at carbon atoms C2 and C3 are less reactive in the sulfation process (Zhang et al. 2011, Roy et al. 2009). The results obtained for cellulose sulfation by sulfamic acid–urea mixture confirm this conclusion. The special methods of OH-groups protection should be used to obtain regioselective cellulose sulfates (Fox et al. 2011, Zhang et al. 2010).

Developed method of cellulose sulfation by sulfamic acid–urea mixture has a number of advantages: sulfamic acid is less corrosive and less toxic than the traditionally used sulphating agents. In contrast to cellulose sulfation by sulfamic acid in the absence of urea (Wagenknecht et al. 1993, Zhang et al. 2011) the developed method allows to obtain cellulose sulphates with more high DS_s to reduce the cellulose destruction and the reaction time.

4 Conclusion

New method of cellulose sulfates obtaining from aspen wood was developed. This method integrates the stages of green peroxide catalytic delignification of wood in acetic acid – water medium and of cellulose sulfation by less-aggressive and less-toxic sulfating agent – sulfamic acid–urea mixture.

First the environmentally safe solid catalyst TiO₂ was used for one-step obtaining of pure cellulose from aspen wood in the medium H₂O₂–CH₃COOH–H₂O at temperatures ≤100°C and atmospheric pressure.

At selected conditions of wood peroxide delignification (100 °C, 5 % H₂O₂, 25 % CH₃COOH, 1 % TiO₂, LWR 15, time 4 h) the cellulosic product containing 93.5 % cellulose, 5.5 % hemicelluloses and 0.7 % lignin was obtained with the yield 50 %.

The conditions of effective sulfation of cellulosic product by sulfamic acid–urea mixture were selected. In contrast to cellulose sulfation by sulfamic acid in the absence of urea they allow to obtain the cellulose sulfates with the higher degree of substitution (up to 1.5). The yield of cellulose sulfates prepared in diglyme solvent was by 2.5 times higher than that in the medium of DMF.

Acknowledgments

The reported study was supported by Russian Science Foundation, grant № 16-13-10326.

References

- Al-Horani RA, Desai UR (2010) Chemical sulfation of small molecules – advances and challenges. *Tetrahedron* 66:2907–2918
- ASTM D1795 - 13 Standard Test Method for Intrinsic Viscosity of Cellulose
- Chen G, Zhang B, Zhao J, Chen H (2013) Improved process for the production of cellulose sulfate using sulfuric acid/ethanol solution. *Carbohydr Polym* 95:332–337
- Fengel D (1992) Characterization of cellulose by deconvoluting the OH valence range in FTIR spectra. *Holzforschung* 46:283–288

- Fox SC., Li B, Xu D, Edgar KJ (2011) Regioselective esterification and etherification of cellulose: a review. *Biomacromolecules* 12:P 1956–1972
- Gericke M, Liebert T, Heinze T (2009) Interaction of ionic liquids with polysaccharides, 8 - synthesis of cellulose sulfates suitable for polyelectrolyte complex formation. *Macromol Biosci* 9:343–353
- Hallac BB, Ragauskas AJ (2011) Analyzing cellulose degree of polymerization and its relevancy to cellulosic ethanol. *Biofuels Bioprod Bioref* 5:215–225
- Hu F, Jung S, Ragauskas A (2012) Pseudo-lignin formation and its impact on enzymatic hydrolysis. *Bioresource Technol* 117:7–12
- Huang X, Zhang WD (2012) Preparation of cellulose sulfate and evaluation of its properties. *Journal of Fiber Bioengineering and Informatics* 3:32–39
- Kuznetsov BN, Kuznetsova SA, Levdansky VA, Levdansky AV, Vasil'eva NYu, Chesnokov NV, Ivanchenko NM, Djakovitch L, Pinel C (2015) Optimized methods for obtaining cellulose and cellulose sulfates from birch wood. *Wood Sci Technol* 49:825–843
- Kuznetsov BN, Sudakova IG, Garyntseva NV, Djakovitch L, Pinel C (2013) Kinetic study of aspen-wood sawdust delignification by H₂O₂ with sulfuric acid catalyst under the mild conditions. *Reac Kinet Mech Cat* 110:271–280
- Kuznetsov BN, Tarabanko VE, Kuznetsova SA (2008) New catalytic methods for obtaining cellulose and other chemical products from vegetable biomass. *Kinet Catal +* 49:517–526
- Lin N, Huang J, Dufresne A (2012) Preparation, properties and applications of polysaccharide nanocrystals in advanced functional nanomaterials: a review. *Nanoscale* 4:3274–3294
- Nishiyama Y, Langan P, Chanzy H (20002) Crystal structure and hydrogen-bonding system in cellulose I β from synchrotron X-ray and neutron fiber diffraction. *J Am Chem Soc* 124:9074–9082
- Park S, Baker JO, Himmel ME, Parilla PA, Jonson DK (2010) Cellulose crystallinity index: measurement techniques and their impact on interpreting cellulase performance. *Biotechnol Biofuels* 3:10
- Qin Z, Ji L, Yin X, Zhu L, Lin Q, Qin J (2014) Synthesis and characterization of bacterial cellulose sulfates using a SO₃/pyridine complex in DMAc/LiCl. *Carbohydr Polym* 101:947–953
- Oberlerchner JT, Rosenau T, Potthast A (2015) Overview of Methods for the Direct Molar Mass Determination of Cellulose. *Molecules* 20: 10313-10341
- Rossberg C, Steffien D, Bremer M, Koenig S, Carvalheiro F, Duarte LC, Moniz P, Hoernicke M, Bertau M, Fischer S (2014) Pulp properties resulting from different pretreatments of wheat straw and their influence on enzymatic hydrolysis rate. *Bioresource Technology* 169 : 206–212.
- Roy D, Semsarilar M, Guthrie JT, Perrier S (2009) Cellulose modification by polymer grafting: a review. *Chem Soc Rev* 38: 2046–2064
- Shibata T (2011) Cellulose and Its Derivatives in Medical Use. In: Peter A Williams (ed) *Renewable Resources for Functional Polymers and Biomaterials: Polysaccharides, Proteins and Polyesters*, RSC Publishing; Cambridge, pp 48–87
- Sixta H (2006) *Handbook of pulp*. Wiley – VCH Verlag SmbH & Co, Weinheim, Germany
- Sjöström E, Alen R (1999) *Analytical methods in wood chemistry, pulping and papermaking*. Springer Series in Wood Science, Springer-Verlag, Berlin
- TAPPI (1998) (acid- insoluble lignin in wood and pulp-T222 om-02)
- Wagenknecht W, Nehls I, Philipp B (1993) Studies on the regioselectivity of cellulose sulfation in an N₂O₄-N,N-dimethylformamide–cellulose system. *Carbohydr Res* 240:245–252

- Wang ZM, Li L, Xiao KJ, Wu JY (2009) Homogeneous sulfation of bagasse cellulose in an ionic liquid and anticoagulant activity. *Bioresource Technol* 100:1687–1690
- Wang ZM, Li L, Zheng BS, Normakhamatov N, Guo SY (2007) Preparation and anticoagulation activity of sodium cellulose sulfate. *Int J Biol Macromol* 41:376–382
- Wang J, Huang H, Huang X (2016) Molecular weight and the Mark-Houwink relation for ultra-high molecular weight charged polyacrylamide determined using automatic batch mode multi-angle light scattering. *J. Appl. Polym. Sci* 133: 43748-43755
- Zhang K, Brendler E, Fischer S (2010) FT Raman investigation of sodium cellulose sulfate. *Cellulose* 17:427–435
- Zhang K, Brendler E, Geissler A, Fischer S (2011) Synthesis and spectroscopic analysis of cellulose sulfates with regulable total degrees of substitution and sulfation patterns via ^{13}C NMR and FT Raman spectroscopy. *Polymer* 52:26–32
- Zhang Q, Lin D, Yao S (2015) Review on biomedical and bioengineering applications of cellulose sulfate. *Carbohydr Polym* 132:311–322
- Zhu L, Qin J, Yin X, Ji L, Lin Q, Qin Z (2014) Direct sulfation of bacterial cellulose with a $\text{ClSO}_3\text{H}/\text{DMF}$ complex and structure characterization of the sulfates. *Polym Advan Technol* 25:168–172