



**Materials Synthesis, Characterization and DFT Calculations  
of the Visible-Light-Active Perovskite-like Barium  
Bismuthate Ba<sub>1.264</sub>(4)Bi<sub>1.971</sub>(4)O<sub>4</sub> Photocatalyst**

Journal:	<i>Journal of Materials Chemistry C</i>
Manuscript ID	TC-ART-11-2019-006457.R1
Article Type:	Paper
Date Submitted by the Author:	29-Jan-2020
Complete List of Authors:	Shtarev, Dmitry; Far Eastern State Transport University Shtareva, A.V.; Far Eastern State Transport University Kevorkyants, Ruslan; St. Petersburg State University, Photonics Rudakova, A.V.; Saint Petersburg State University Molokeev, Maxim S. ; Kirensky Institute of Physics SB RAS, Bakiev, T.V.; Saint Petersburg State University Bulanin, Kirill; Saint-Petersburg State University, Physics Ryabchuk, V.K.; Saint Petersburg State University Serpone, Nick; Universita di Pavia, Dipartimento di Chimica Organica

# Journal of Materials Chemistry C

Materials for optical, magnetic and electronic devices

## Guidelines for Reviewers

Thank you very much for agreeing to review this manuscript for [Journal of Materials Chemistry C](#).



*Journal of Materials Chemistry C* is a weekly journal in the materials field. The journal is interdisciplinary, publishing work of international significance on all aspects of materials chemistry related to applications in optical, magnetic and electronic devices. Articles cover the fabrication, properties and applications of materials.

*Journal of Materials Chemistry C*'s Impact Factor is **6.641** (2018 Journal Citation Reports®)

---

*The following manuscript has been submitted for consideration as a*  
**FULL PAPER**

---

For acceptance, a Full paper must report primary research that demonstrates significant **novelty and advance**, either in the chemistry used to produce materials or in the properties/ applications of the materials produced. Work submitted that is outside of these criteria will not usually be considered for publication. The materials should also be related to the theme of optical, magnetic and electronic devices.

When preparing your report, please:

- Focus on the **originality, importance, impact** and **reproducibility** of the science.
- Refer to the **journal scope and expectations**.
- **State clearly** whether you think the article should be accepted or rejected and give detailed comments (with references) both to help the Editor to make a decision on the paper and the authors to improve it.
- **Inform the Editor** if there is a conflict of interest, a significant part of the work you cannot review with confidence or if parts of the work have previously been published.
- **Provide your report rapidly** or inform the Editor if you are unable to do so.

Best regards,

**Professor Peter Skabara**  
Editor-in-Chief  
University of Glasgow, UK

**Dr Sam Keltie**  
Executive Editor  
Royal Society of Chemistry

Contact us

Please visit our [reviewer hub](#) for further details of our processes, policies and reviewer responsibilities as well as guidance on how to review, or click the links below.



What to do  
when you  
review



Reviewer  
responsibilities



Process &  
policies

## Responses to Editorial request (ORCID) and reviewers' comments

The ORCIDs of all the authors now appear on page 9 of the manuscript

### Referee: 1

1) Regarding the synthesis, does it go 100% to completion? There was no purification carried out and thus my question

During the preparation of samples, we performed an evaluation of that synthesis of barium bismuthate was 100% completion. With shorter synthesis times, the formation of pure barium bismuthate was not observed. To demonstrate this, relevant results were added to the article, which are given in Section 3.1 and supplementary information.

2) The authors state for the XPS data that "The two Gaussians at 531 eV and 532 eV are associated with the O–C=O bonds of chemisorbed carbon dioxide molecules. The presence of such chemisorbed species on the surface is characteristic of compounds containing alkaline earth metals." In order to truly verify this, the authors should carry out TGA/MS analysis and monitor the m/z value of the evolved gas unless they have already verified it.

The proposed by the reviewer TGA studies were conducted. Figure 1 shows the DTG curve of the studied sample during its annealing in vacuum. Even at high temperatures (higher 500°C), there are no noticeable changes in the mass of the sample.

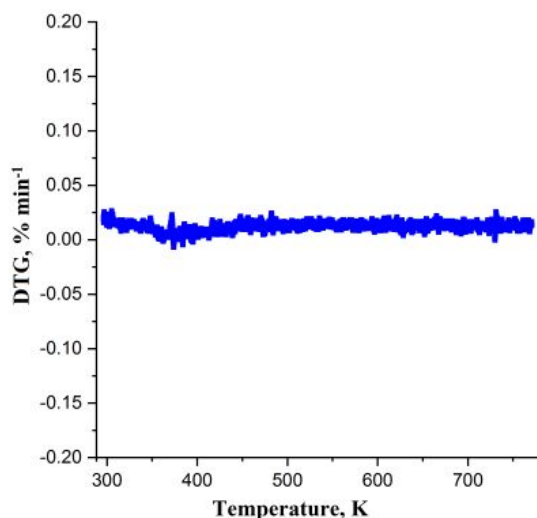


Figure 1. TGA curve of barium bismuthate  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  in vacuum.

The verification of chemisorbed carbon dioxide molecules was made by IR spectroscopy. Prior to the gas-phase IR experiment, the sample was thermally treated at 350°C to reduce the amount of physisorbed water molecules and chemisorbed carbon dioxide species on the bismuthate's surface. Nonetheless, even after such a treatment, the sample surface remained highly hydrated and carbonated. Figure 2 shows the IR spectrum of such a treated barium bismuthate sample (this spectrum is presented as spectrum 3 in Figure S3, in the Electronic Supplementary Information).

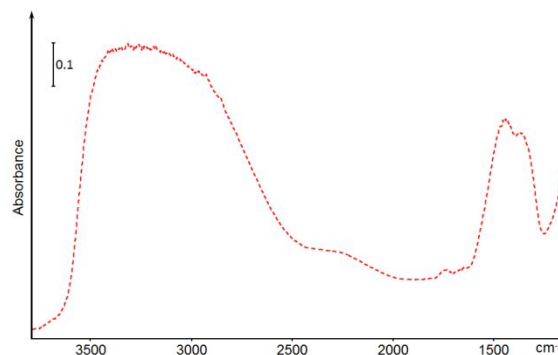


Figure 2. IR spectrum of treated barium bismuthate  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  in vacuum at room temperature before the  $\text{CO}_2$  photoreduction experiment. The sample was preliminary thermo-treated at 350 °C.

The IR spectrum of such a treated barium bismuthate sample revealed a broad absorption of molecular water at 3600–2700  $\text{cm}^{-1}$ . The intense absorption with two maxima at 1363  $\text{cm}^{-1}$  and 1442  $\text{cm}^{-1}$  are caused by the C=O stretching vibrations of surficial carbonates, [F.A. Miller, C.H. Wilkins, *Analytical chemistry*, 1952, 24, 1253-1294; G. Socrates, *Infrared and Raman characteristic group frequencies. Tables and Charts*, Chichester: John Wiley & Sons, New York, 2001.] the presence of which was also detected by XPS spectroscopy. This can be explained by the high affinity of carbon dioxide molecules for the surface of metal oxides containing alkaline-earth metal ions.

It is also interesting that during the reaction, the spectral feature related to the  $\text{CO}_3^{2-}$  carbonates (*ca.* 1442  $\text{cm}^{-1}$ ) decreases in intensity, while the absorption at higher (1700-1500  $\text{cm}^{-1}$ ) and lower (1300-1150  $\text{cm}^{-1}$ ) wavenumbers increased. These spectral regions may be attributed to the bicarbonate C=O stretching vibrations ( $\text{HCO}_3^-$ ).

These findings were presented on page 6 of the manuscript and in the Supplementary Information section.

## **Referee 2:**

1. The first one is that Eq.1 is not introduced or explained. The reader would surely wonder why Eq.1 can be applied in this case. Is it specific of phonons or is it valid for bonds in general?

Equation 1 was taken from reference [F.D. Hardcastle and I.E. Wachs, *The Molecular Structure of Bismuth Oxide by Raman Spectroscopy*, *J. Solid State Chem.* 1992, **97**, 319–331.]. This work was devoted to the study of molecular structure of different bismuth oxides by Raman spectroscopy. As a result, the authors found the empirical bond length/bond strength/Raman stretching frequency relationships and suggested the unique and effective method of interpreting Raman spectra of bismuth oxide species.

Thus, Equation 1 is applicable in the analysis of Raman spectra of compounds containing Bi–O bonds, as in the case of synthesized barium bismuthate  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$ .

Accordingly, we have modified the text on page 3 to read:

“Using the empirical expression (eqn. 1) found for bismuth oxides that relates the Bi–O bond lengths ( $R$ ) to the Raman stretching frequencies in  $\text{cm}^{-1}$  ( $\nu$ )<sup>42</sup> makes it possible to calculate the bond lengths for the Bi–O vibrations at  $647 \text{ cm}^{-1}$  and  $315 \text{ cm}^{-1}$  of studied sample.”

$$\nu = 92760e^{-2.511R} \quad (1)$$

2. The second one is about the DFT frequency estimates. Did the authors try alternative methods to calculate them respect to the traditional one implemented in their suite of code, such as DFPT or a finite difference approach accounting for the potential energy surface curvature?

We apologize for rather not understanding the reviewer's point here. Suffices to say that in the presented work, no (phonon) frequencies were computed.

3. Finally, I advise the authors to better explain how the flatband potential measurements have been performed.

To the extent that flatband potentials are determined electrochemically/photoelectrochemically, techniques that were not used in the present work, we have modified the relevant text to state “energy or energies” of the VB and/or CB.

## ARTICLE

# Materials Synthesis, Characterization and DFT Calculations of the Visible-Light-Active Perovskite-like Barium Bismuthate $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$ Photocatalyst

D.S. Shtarev,<sup>a,b</sup> A.V. Shtareva,<sup>a,b</sup> R. Kevorkyants,<sup>c</sup> A.V. Rudakova,<sup>c</sup> M.S. Molokeyev,<sup>b,d,e</sup> T.V. Bakiev,<sup>c</sup> K.M. Bulanin,<sup>c,f</sup> V.K. Ryabchuk,<sup>c,f</sup> and N. Serpone<sup>g,\*</sup>

A perovskite-like barium bismuthate of the  $\text{BaBi}_2\text{O}_4$  class,  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$ , has been prepared by a solid-state synthesis and subsequently characterized by a number of experimental techniques (XPS, DRS, SEM, EDX and Raman spectra), as well as by a DFT computational approach using the GGA Perdew-Burke-Ernzerhof (PBE) density functional to determine the energy band structure. XRD peaks were indexed to a rhombohedral cell ( $R\text{-}3m$ ) with parameters close to  $\text{Ba}_{0.156}\text{Bi}_{0.844}\text{O}_{1.422}$  (i.e., to  $\text{Ba}_{0.439}\text{Bi}_{2.374}\text{O}_4$ ), which upon a Rietveld refinement gave  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$ . Bi–O bond lengths determined from this refinement (1.86 and 2.31 Å) accorded with bond lengths estimated from Raman spectra (1.97 and 2.26 Å). DFT calculations revealed the bismuthate to display two bandgaps that correspond to lower-energy indirect (2.28 eV) and to higher-energy direct (2.36 eV) electronic transitions in good agreement with the experimental bandgaps of 2.26 eV and 2.43 eV, respectively, from Tauc plots of DRS spectra. Relative to the indirect bandgap energy of 2.26 eV, the energies of the valence band and of the conduction band were, respectively, +1.14 eV and –1.12 eV. The photoactivity of  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  was examined toward the photoreduction of the greenhouse gas  $\text{CO}_2$  in aqueous media photoelectrochemically yielding alcohols and alkanes, while in the gas phase in an infrared cell reactor the products were carbon monoxide and alkanes.

Received 25<sup>th</sup> November 2019,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

## 1. Introduction

The search for novel visible-light-active (VLA) semiconductor photocatalysts has been an active field of investigations for several decades.<sup>1–4</sup> Such materials have typically found applications in a number of significant areas: (i) purification of water and air contaminated with organic/inorganic pollutants (ecology), (ii)

photocatalytic decomposition of water (more precisely, water splitting to produce a solar fuel; energy), and (iii) environmental reduction of the greenhouse gas  $\text{CO}_2$  to produce a solar fuel such as  $\text{CH}_4$  and/or  $\text{CH}_3\text{OH}$  among others (ecology and energy).

Within the present context, a number of experimental<sup>5</sup> and theoretical<sup>6,7</sup> studies have reported an anomalous ratio in a series of alkaline-earth bismuthates between bandgap width and the energy of the conduction band. In particular, bismuthates of heavy alkaline-earth metals (e.g., those of Sr and Ba) are expected to demonstrate the lowest potentials of the conduction band together with reasonable bandgap energies. In this regard, the photocatalytic properties of some basic strontium bismuthates have been reported.<sup>5,8–13</sup> Of these, only the barium bismuthate double perovskite  $\text{Ba}_2\text{Bi}^{3+}\text{Bi}^{5+}\text{O}_6$  (empirically,  $\text{BaBiO}_3$ ) has been examined systematically in a number of photocatalytic studies.<sup>14–18</sup> For instance, Lee and coworkers<sup>14</sup> showed that this material is a p-type semiconductor, which has been shown to act as a photocatalyst in a number of reactions including photocatalytic water splitting.<sup>15–18</sup> However, determination of its bandgap has revealed a large discrepancy between theory and experiment; theory predicted a bandgap of 1.00–1.45 eV,<sup>19–21</sup> whereas experiments placed the bandgap substantially greater at 1.41–2.05 eV.<sup>15–18,22,23</sup> Presumably, this inconsistency is likely caused by the two oxidation states of bismuth present in the structure (viz.,  $\text{Bi}^{3+}$  and  $\text{Bi}^{5+}$ ).

The critical intrinsic limitation on the use of novel semiconducting photocatalysts is their bandgap energy. Visible light photoactivation of such materials is possible only if their bandgaps do not exceed 3.3 eV (see e.g., ref. [24] and refs. therein). Depending on the particular application, additional limitations could

<sup>a</sup> Yu. A. Kosygin Institute of Tectonics and Geophysics, Far Eastern branch of the Russian Academy of Sciences, 65 Kim Yu Chen Street, Khabarovsk, 680063 Russian Federation; [shtarev@mail.ru](mailto:shtarev@mail.ru) and [avshtareva@mail.ru](mailto:avshtareva@mail.ru)

<sup>b</sup> Far Eastern State Transport University, 47 Seryshev Street, Khabarovsk, 680021 Russian Federation; [msmolokeyev@mail.ru](mailto:msmolokeyev@mail.ru)

<sup>c</sup> Saint-Petersburg State University, Laboratory "Photoactive Nanocomposite Materials", Ul'yanovskaya 1, Peterhof, Saint-Petersburg, 198904, Russian Federation; [ruslan.kevorkyants@gmail.com](mailto:ruslan.kevorkyants@gmail.com), [aida.rudakova@spbu.ru](mailto:aida.rudakova@spbu.ru), [tairbakiev@gmail.com](mailto:tairbakiev@gmail.com)

<sup>d</sup> Kirensky Institute of Physics, Akademgorodok 50, bld. 38, Krasnoyarsk, 660036 Russian Federation; [msmolokeyev@mail.ru](mailto:msmolokeyev@mail.ru)

<sup>e</sup> Siberian Federal University, 79 Svobodny pr., 660041 Krasnoyarsk, Russian Federation; email: [msmolokeyev@mail.ru](mailto:msmolokeyev@mail.ru)

<sup>f</sup> Saint-Petersburg State University, Department of Photonics, Ul'yanovskaya 1, Peterhof, Saint-Petersburg, 198904 Russian Federation; [v.ryabchuk@spbu.ru](mailto:v.ryabchuk@spbu.ru) and [k.bulanin@spbu.ru](mailto:k.bulanin@spbu.ru)

<sup>g,\*</sup> PhotoGreen Laboratory, Dipartimento di Chimica, Università di Pavia, via Taramelli 12, Pavia 27100, Italia; [nick.serpone@unipv.it](mailto:nick.serpone@unipv.it)

<sup>#</sup> Scheme of the PEC cell system, chromatograms of the photoreduction of  $\text{CO}_2$ , EDX spectral results and XPS spectra data together with FTIR evidence of  $\text{CO}_2$  photoreduction products, and the time course of the (non)degradation of phenol are given in the Electronic Supplementary Information (ESI):  
See DOI: 10.1039/x0xx00000x

be imposed on the fundamental properties of such materials as, for instance, the redox potentials of the valence band ( $E_{VB}$ ) and the conduction band ( $E_{CB}$ ).

While the photocatalytic water splitting process is an ecofriendly source of energy ( $H_2$  as the fuel), reduction of  $CO_2$  to other more useful substrates is, in addition to energy generation, a means to potentially reduce the controversial threat of global warming by diminishing the atmospheric concentration of this greenhouse gas. This is substantiated by the increasing number of publications associated with the photoreduction of  $CO_2$  vis-à-vis a decreasing number of publications during the last two years with regard to the water splitting process.<sup>4</sup>

Occurrence of the photocatalytic water splitting process requires the redox potential of the conduction band to be negative because  $E(H^+/H_2) = 0.00$  V (versus the NHE scale) and for the valence band to be  $>1.23$  eV because  $E(O_2/H_2O) = 1.23$  V at pH 7. By contrast, the photoreduction of  $CO_2$  may take place when  $E_{CB} < -0.24$  to  $-0.61$  V as the relevant redox potentials of its half-reactions are in this range. According to empirical models for a set of simple oxides,<sup>25</sup> the lowering of the conduction band level is accompanied by an increase of the bandgap width, which drastically limits the choice of materials suitable for a practical photoreduction of  $CO_2$ .

Our current study reports (for the first time) a systematic theoretical and experimental study of another promising perovskite-like barium bismuthate of the  $BaBi_2O_4$  class, with regard to its synthesis and characterization of the structure, electronic, and optical properties, together with its visible-light-photoactivity toward the photoinduced reduction of the greenhouse gas carbon dioxide.

## 2. Results and discussion

### 2.1 Structure and composition of the as-synthesized barium bismuthate

The structure and the unit cell composition of the as-synthesized barium bismuthate were investigated by X-ray diffraction methods.

Figure 1 displays the XRD pattern of the barium bismuthate and the results of the Rietveld analysis.

All peaks were indexed to a rhombohedral cell ( $R-3m$ ) with parameters that were close to  $Ba_{0.156}Bi_{0.844}O_{1.422}$  (or, that is, to  $Ba_{0.439}Bi_{2.374}O_4$ ).<sup>26</sup>

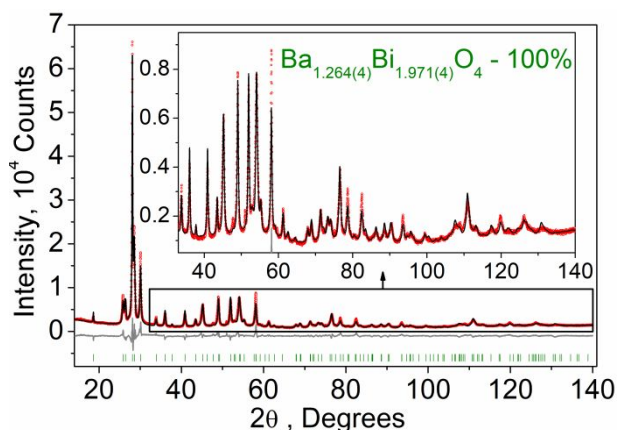


Figure 1. Difference Rietveld plot of  $Ba_{1.264(4)}Bi_{1.971(4)}O_4$ . Red dots depict the experimental XRD powder pattern; the black solid line shows the pattern calculated from the structure; the grey solid line below refers to the difference between experimental and calculated patterns; the green vertical lines depict the Bragg peak

positions. The inset shows an enlarged view of the plot and the chemical formula of the compound investigated.


Consequently, this crystal structure was taken as the starting model for a Rietveld refinement. The occupation values of all ions were refined with no restraints. The refinement was stable and gave low  $R$ -factors (Table 1,

Figure 2). Coordinates of the atoms and main bond lengths are collected in Tables 2 and 3, respectively. The chemical formula obtained from the refinement could thus be written as  $Ba_{1.264(4)}Bi_{1.971(4)}O_4$  (

Figure 1). The small sum of the charges (+0.44) implies that the number of oxygen vacancies in the structure is overestimated, which is often the case in such systems because of difficulties in refining the occupancy of light ions in the presence of heavy metal ions. Thus, it could be argued that the perovskite-like barium bismuthate of the  $BaBi_2O_4$ -type was successfully synthesized.<sup>27</sup>

Table 1. Main parameters from the processing and refinement of the  $Ba_{1.264(4)}Bi_{1.971(4)}O_4$  system.

Compound	$Ba_{1.264(4)}Bi_{1.971(4)}O_4$
Space group	$R-3m$
$a$ , Å	4.0069 (3)
$c$ , Å	28.534 (2)
$V$ , Å <sup>3</sup>	396.74 (5)
$2\theta$ -interval, degrees	15–140
$R_{wp}$ , %	8.07
$R_p$ , %	5.99
$R_{exp}$ , %	2.22
$\chi^2$	3.64
$R_B$ , %	3.39

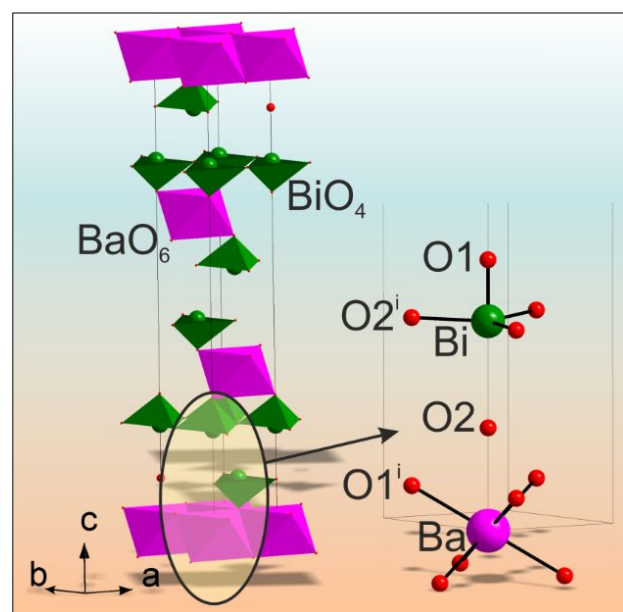

**Figure 2.** The crystal structure of  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$ . Purple octahedra denote the  $\text{BaO}_6$  function; green trigonal pyramids refer to the  $\text{BiO}_4$  functions with the green Bi atom inside; red spheres denote the oxide ions. Ions with the “i” label depict symmetrically equivalent ions.

**Table 2.** Fractional atomic coordinates and isotropic displacement parameters ( $\text{\AA}^2$ ) of  $\text{BaBi}_2\text{O}_4$ .

	x	y	z	$B_{\text{iso}}$	Occupancy
Ba	0	0	0	0.7 (2)	0.529 (2)
Bi	0	0	0.22227 (3)	0.3 (2)	0.4121 (8)
O(1)	0	0	0.2874 (3)	2.0 (5)	0.569 (5)
O(2)	0	0	0.109 (1)	2.0 (7)	0.268 (4)

**Table 3.** Main bond lengths ( $\text{\AA}$ ) of  $\text{BaBi}_2\text{O}_4$  (Symmetry codes: (i)  $-x-1/3, -x+y+1/3, -z+1/3$ ).

$\text{Ba}(1)-\text{O}(1)^{\text{i}}$	2.660 (5)
$\text{Bi}(1)-\text{O}(1)$	1.86 (1)
$\text{Bi}(1)-\text{O}(2)^{\text{i}}$	2.3140 (7)


Four main characteristic spectral ranges were identified in the Raman spectrum of the synthesized barium bismuthate sample (spectrum shown in **Figure 3**): (1) the broad peak at  $215-300\text{ cm}^{-1}$  is assigned to Ba–O vibrations,<sup>28</sup> (2) the noticeable high-frequency shoulder in the  $300-330\text{ cm}^{-1}$  range is ascribed to Bi–O–Bi asymmetric stretch vibrations,<sup>29</sup> (3) the peak at  $515\text{ cm}^{-1}$  is due to Ba–O vibrations,<sup>29</sup> while (4) the most intense and narrow peak at  $647\text{ cm}^{-1}$  corresponds to the Bi–O<sup>−</sup> stretching modes.<sup>30,31</sup>

Using the empirical expression (eqn. 1) found for bismuth oxides that relates the Bi–O bond lengths ( $R$ ) to the Raman stretching frequencies in  $\text{cm}^{-1}$  ( $\nu$ )<sup>32</sup> makes it possible to calculate the bond lengths for the Bi–O vibrations at  $647\text{ cm}^{-1}$  and  $315\text{ cm}^{-1}$  of studied sample.

$$\nu = 92760e^{-2.511R} \quad (1)$$


The bond lengths thus estimated are  $1.97\text{ \AA}$  and  $2.26\text{ \AA}$ , respectively, which correspond to the lengths for the  $\text{Bi}(1)-\text{O}(1)$  and  $\text{Bi}(1)-\text{O}(2)^{\text{i}}$  bonds determined from the Rietveld refinement for the  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  compound (**Table 3** and **Figure 2**).

**Figure 4** illustrates the scanning electron microscopy (SEM) images of the synthesized barium bismuthate particle. Evidently, the particles tend to be rather large ( $20\text{ }\mu\text{m}$ ) and possess a poorly developed surface, albeit a layered structure. This is especially noticeable in **Figure 4b**.

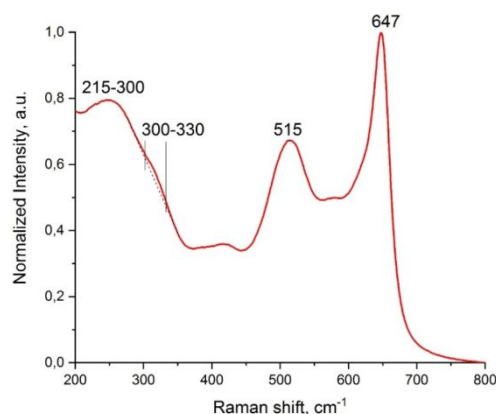

**Figure 3.** Raman spectrum of the as-synthesized barium bismuthate,  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$ , sample.

The particles are agglomerates of ‘scales’ that could be a result of the powder pressing during the sample preparation procedure (see Synthesis and characterization section).

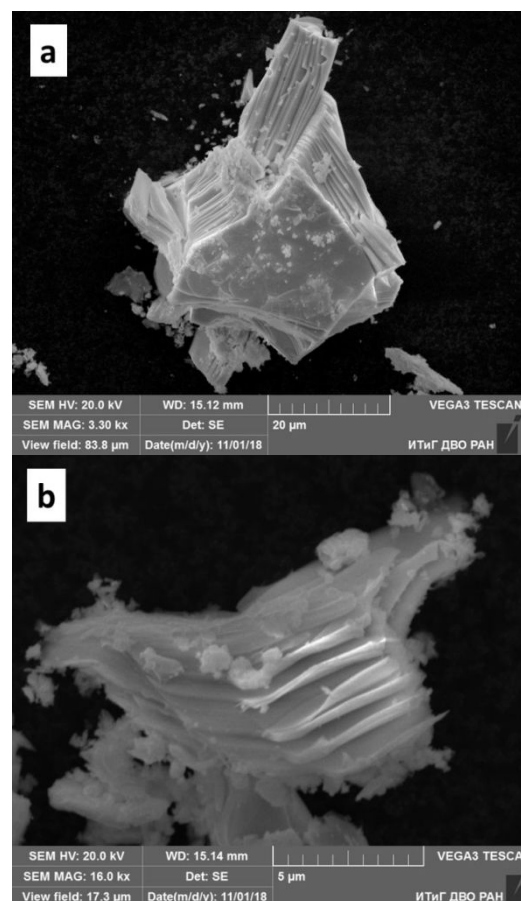

**Figure 4.** SEM images of barium bismuthate synthesized particles.

The specific surface area determined by the BET technique was *ca.*  $0.5\text{ m}^2\text{ g}^{-1}$  that corresponds to a practically non-porous sample. Data on surface morphology are consistent with the SEM micro-images.

EDX spectra of the as-synthesized barium bismuthate particle (reported in **Figure S1** in the Electronic Supplementary Information; ESI) shows that all chemical elements (Ba, Bi, O) in the compound



are regularly distributed over its volume. No impurity elements were observed.

The elemental composition of the sample's surface was analyzed using XPS techniques (spectra illustrated in Figure S2). The XPS data infer that barium and bismuth are present in single oxidation states, namely  $\text{Ba}^{2+}$  and  $\text{Bi}^{3+}$ . The oxygen line demonstrates a more complex structure and can be represented as a sum of four Gaussians (see Figure S2c). The two Gaussians at 531 eV and 532 eV are associated with the O–C=O bonds of chemisorbed carbon dioxide molecules. The presence of such chemisorbed species on the surface is characteristic of compounds containing alkaline earth metals. The other two lower-energy spectral lines correspond to oxygen in different oxidation states. The binding energy (BE) peak at 529.4 eV is due to the oxygen dianion  $\text{O}^{2-}$ , whereas the peak at 530.6 eV can be assigned to the oxide anion  $\text{O}^-$ , in agreement with that obtained from the Rietveld refinement of the chemical formula in that the  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  compound is partially positively overcharged (+0.44) owing to the presence of oxygen vacancies. Apparently, the presence of anion vacancies is typical of alkaline earth metal bismuthates. In this regard, various oxygen vacancies in strontium bismuthates have been established by Shtarev and coworkers.<sup>5</sup>

## 2.2. Electronic band structure of the barium bismuthate

The electronic band structure includes the energy position of the edges of the conduction (CB) and valence (VB) bands with respect to the vacuum level. The positions of the conduction ( $E_{\text{CB}}$ ) and valence ( $E_{\text{VB}}$ ) bands, together with the bandgap energies ( $E_{\text{g}}$ ), can be determined experimentally by measuring at least any two of these three values (i.e.,  $E_{\text{CB}}$  and  $E_{\text{g}}$  or  $E_{\text{VB}}$  and  $E_{\text{g}}$ ). Note that knowledge of such an energy level diagram of the material under examination facilitates placing the electrochemical potentials of important redox reactions relative to CB and VB.

For the barium bismuthate  $\text{BaBi}_2\text{O}_4$ , the valence band and the bandgap energies were measured experimentally by X-ray photoelectron spectroscopic (XPS) techniques and by Tauc plots, respectively. The top of the valence band for the  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  sample was determined using the low-energy edge of the XPS spectrum in the  $\text{O}2p$  region (Figure 5), which gave +1.14 eV (relative to NHE) as the energy position of the top of the valence band.<sup>33</sup>

The bandgap energy for the  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  sample was determined using DRS methods. The absorption spectrum displayed in Figure 6a clearly demonstrates that the material absorbs light well into the visible range. Moreover, the reflectance ( $> 0.8$ ) near the edge of the *intrinsic* absorption allows the use of the Kubelka–Munk transformation and the application of the Tauc method in determining the bandgap energy. Tauc plots for both direct (value of the exponent is 2) and indirect (value of the exponent is 1/2) allowed electronic transitions are reported in Figure 6b; extrapolation of the linear regions of the plots yielded 2.43 eV for the direct bandgap and 2.26 eV for an indirect bandgap.

In addition to spectroscopic studies, the electronic band structure of  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  was also modeled using DFT calculations, results of which are presented in Figure 7 for the computed electronic band structure and the density of states. Results from these DFT calculations suggest that the bismuthate displays two bandgaps that correspond to lower-energy indirect (2.28 eV) and to higher-energy direct (2.36 eV) electronic transitions. A comparison of the experimental and theoretical bandgaps (compare Figure 6b with Figure 7a) reveals good

agreement between the experimental (2.26 eV) and the computed (2.28 eV) indirect bandgap. The theoretically calculated direct

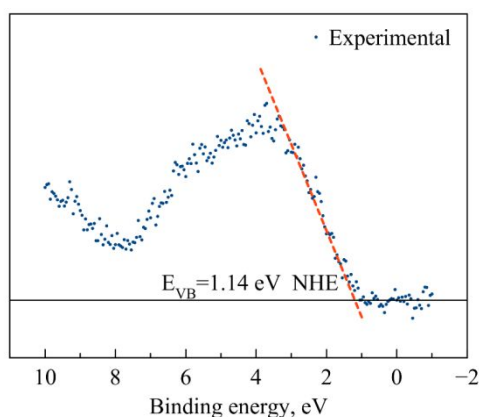


Figure 5. XPS spectrum of the synthesized  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  bismuthate sample in the  $\text{O}2p$  region. The horizontal black line is the XPS baseline, whereas the dashed red line is the linear extrapolation of the low-energy edge of the spectrum. The binding energy scale is presented relative to NHE in accordance with the methodology given in reference [33].


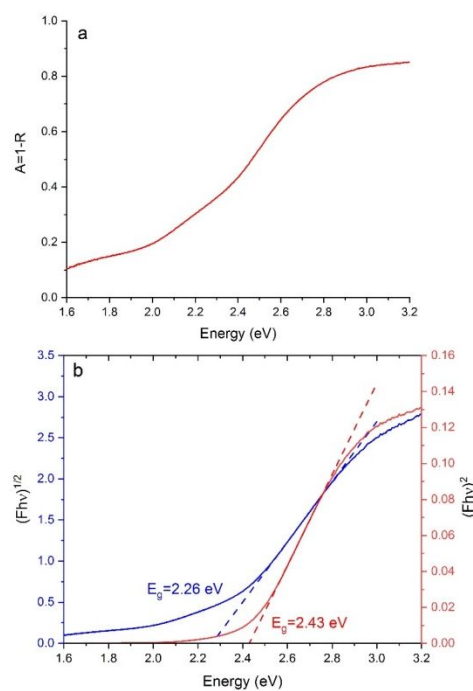


Figure 6. (a) Diffuse reflectance spectra displayed as absorbance  $A = (1 - R)$  spectra of the barium bismuthate sample. (b) Tauc plot assuming direct (red) and indirect (blue) electronic transitions.

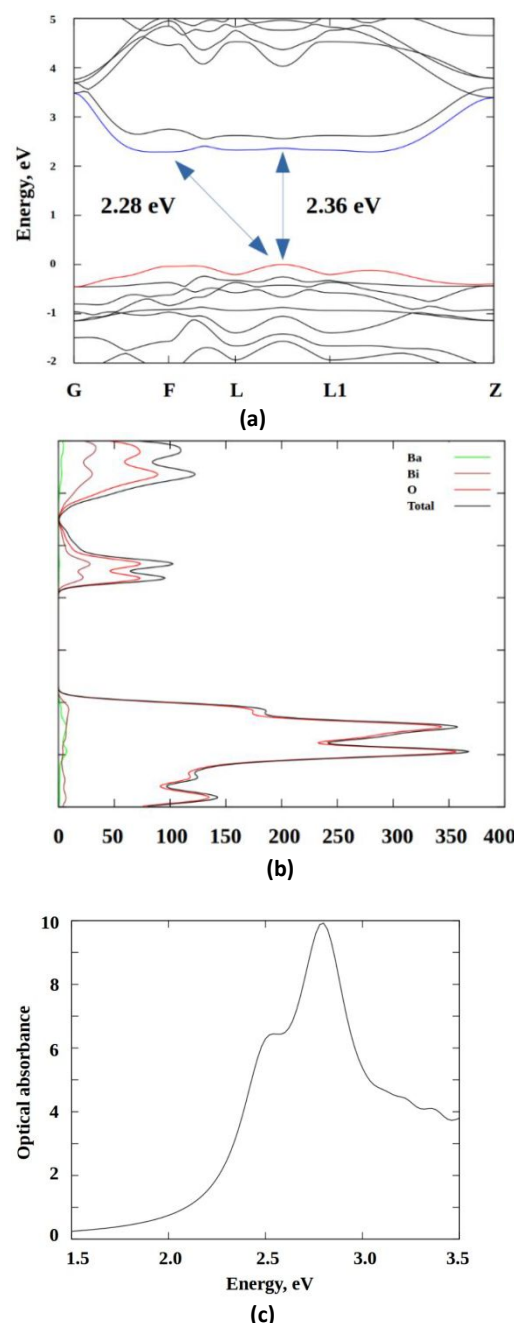

**Figure 7.** Electronic band structure (a) and density of states (b), together with the computed optical absorption spectrum (c) of the barium bismuthate system.


bandgap of 2.36 eV is also in fairly good accord with its experimental counterpart (2.43 eV). To the extent that theoretical calculations predict indirect allowed transitions, we used the experimental bandgap of 2.26 eV to construct the band diagram of the  $\text{BaBi}_2\text{O}_4$ -type bismuthate.

The calculated density of states of the barium bismuthate indicates that the valence band is formed only by oxygen-related orbitals, while the conduction band is a mixture of bismuth and oxygen orbitals (see **Figure 7b**). **Figure 7c** illustrates the calculated optical absorption spectrum of the barium bismuthate; the lower-energy indirect transition is seen as being less intense than the higher-energy direct transition. Both peaks appear to be blue-shifted by  $\sim 0.2$  eV relative to the corresponding energies of the electronic transitions displayed in **Figure 7a**.

Usage of the energy for the valence band ( $E_{\text{VB}} = +1.14$  eV vs. NHE) and the bandgap energy  $E_{\text{g}}$  (2.26 eV) made it possible to determine the energy of the bottom of the conduction band:  $E_{\text{CB}} = -1.22$  eV. The relevant band structure of the  $\text{BaBi}_2\text{O}_4$ -type bismuthate is presented in **Figure 8**, together with the redox potentials of some important half-reactions.

### 2.3. Photoactivity of the $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$ bismuthate toward $\text{CO}_2$ reduction

The relative arrangement of energy bands and half-reaction potentials displayed in **Figure 8** suggest that the bismuthate is a suitable material for carrying out the reduction of carbon dioxide and the formation of superoxide radical anions. The potentials

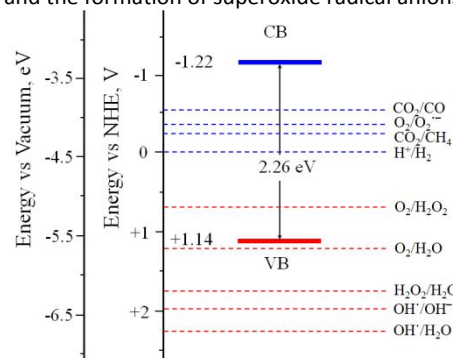

**Figure 8.** Positions of the energy bands of the  $\text{BaBi}_2\text{O}_4$ -type barium bismuthate,  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$ , with respect to vacuum and with the electrochemical NHE scale. The positions of the top of the valence band (VB) and the bottom of the conduction band (CB) are manifested by solid red and blue lines, respectively. Dashed lines denote some electrochemical potentials of some important oxidation (red) and reduction (blue) half-reactions.

of most oxidation reactions (production of oxygen or hydrogen peroxide from water, and/or formation of  $\bullet\text{OH}$  radicals) lie below the top of the valence band of the  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  bismuthate so that these reactions are not expected to occur. However, under acidic conditions and in the presence of oxygen, reverse reactions may occur that might lead to corrosion of the bismuthate. Accordingly, confirmation of such an inference was obtained by carrying out the photoreduction of  $\text{CO}_2$  chosen to explore the photocatalytic activity of the as-synthesized barium bismuthate sample assessed photoelectro-chemically in aqueous media in the PEC cell, and spectroscopically by IR techniques in the gas phase using an IR cell reactor.

The PEC cell used in the photoelectrochemical experiment consisted of two-compartment cathode-anode tandem system comprised of the  $(\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4/\text{Ag})-(\text{TiO}_2/\text{FTO})$  tandem where  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4/\text{Ag}$  was the photocathode and the  $\text{TiO}_2/\text{FTO}$  was the photoanode. The preparations of the electrodes and the experimental details have been described elsewhere (see Experimental). The photocathode compartment was filled with an oxygen-free  $\text{KHCO}_3$  aqueous solution, while the photoanode compartment contained an  $(\text{NH}_4)_2\text{C}_2\text{O}_4$  aqueous solution.

The successful course of the photoreduction of  $\text{CO}_2$  in the photoelectrochemical cell was observed both visually and then confirmed by a chromatographic analysis. Gas evolution was seen both in the photocathode and in the photoanode compartments of the photoelectrochemical cell. Relevant chromatograms of the liquid samples collected from the photocathode compartment before and during the photoprocess are illustrated in **Figure 9**.

The principal changes in the chromatograms occur in the retention time regions of 300, 500 and 600 sec. Additional detailed chromatograms covering these time intervals are also reported in **Figure S4**. Reaction products were identified using predefined

retention times of various substances that were suspected as possible products (Figure S5). During the search procedure for products, the confidence interval of the occurrence of the chromatographic peaks of the tested possible products could be superimposed on the analyzed experimental peaks.

Results of chromatographic analyses showed that methanol and ethanol were the principal products that appeared after the first 2 hrs of irradiation of the photocathode compartment (Figure S6). Over the subsequent 2 hrs of irradiation, the quantity of these two products decreased significantly, while ethane formed and increased at the same time. The concentrations of reaction products (Table 4) were determined using calibration curves of the tested substrates.

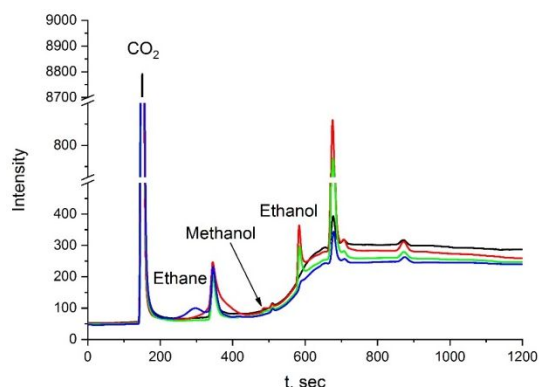


Figure 9. Chromatograms of liquid samples from the cathode compartment of the PEC cell before and during the photoelectrochemical reaction: before irradiation (black) and after 1 hr of irradiation (red), green after 2 hrs, and blue after 4 hrs.

Table 4. Concentrations of the main reaction products from the photocathode compartment of the photoelectrochemical cell.

Irradiation time, hrs	Concentration of reduction products, mM		
	Methanol	Ethanol	Ethane
0	0	0	0
1	0.67	3.86	0
2	0.47	2.63	0
4	0.035	0.38	2.64

Based on the results of the chromatographic analyses, a tentative mechanism of the photoprocesses occurring in such a tandem system can thus be described; it is schematically illustrated in Figure 10. When the photocathode and photoanode are both irradiated with light from the xenon lamp, photoexcitation of the barium bismuthate and the titanium dioxide led to the generation of electron/hole pairs. The photoelectrons at the photocathode participate in the photoreduction of carbon dioxide (present on the photocathode surface as carbonate ions) to alcohols and hydrocarbons, while the photoholes at the photoanode compartment are mainly spent in the oxidation of oxalate ions with formation of carbon dioxide. The membrane separating the two compartments of the PEC cell is permeable to migration of protons into the photocathode compartment, so that released protons are consumed in the reductive half-reactions. In turn, the photoholes accumulated on the silver substrate of the photocathode recombine with the photoelectrons on the FTO substrate of the photoanode. The initial photocurrent was 450  $\mu\text{A}$ , which dropped to 300  $\mu\text{A}$  throughout the photoreaction.

In order to exclude the possibility that the contact of the  $\text{HCO}_3^-$ -containing electrolyte with the silver in the photocathode compartment might lead to the possible photoreduction of carbon dioxide, a blank experiment was carried out under otherwise identical experimental conditions in the (Ag)-(TiO<sub>2</sub>/FTO) tandem system but without the barium bismuthate, where Ag and TiO<sub>2</sub>/FTO were the photocathode and photoanode, respectively. No products were detected by gas chromatography in the liquid samples collected from the photocathode compartment of the PEC cell after irradiation of the system for 5 hrs.

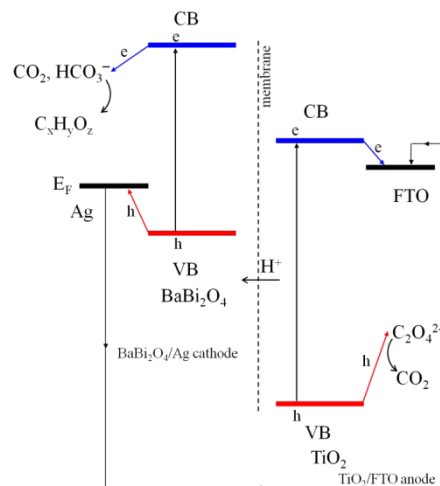


Figure 10. Proposed scheme of the processes occurring in the photoelectrochemical cell in the Ba<sub>1.264(4)</sub>Bi<sub>1.971(4)</sub>O<sub>4</sub>/Ag photocathode compartment and in the TiO<sub>2</sub>/FTO photoanode compartment.

The photoreduction of CO<sub>2</sub> gas in the gas/solid system was also carried out in the IR cell. Prior to the gas-phase experiment, the sample was thermally treated at 350 °C to reduce the amount of physisorbed water molecules and chemisorbed carbon dioxide species on the bismuthate's surface. Nonetheless, even after such a treatment, the sample surface remained highly hydrated and carbonated.

After introduction of CO<sub>2</sub> gas (10 Torr in equilibrium) into the IR cell reactor, the sample was irradiated by the Xe lamp at ambient temperature. The IR spectrum of such a treated barium bismuthate sample (Figure S3, spectrum 3) revealed a broad absorption of molecular water at 3600–2700 cm<sup>-1</sup>. The intense absorption with two maxima at 1363 cm<sup>-1</sup> and 1442 cm<sup>-1</sup> are caused by the C=O stretching vibrations of surficial carbonates,<sup>34,35</sup> the presence of which was also detected by XPS spectroscopy. This can be explained by the high affinity of carbon dioxide molecules for the surface of metal oxides containing alkaline-earth metal ions.

Difference IR spectra of barium bismuthate after irradiating the sample for 30 min (spectrum 1), and 100 min (spectrum 2) are also displayed in Figure S3. Irradiation led to the removal of carbonates and water molecules adsorbed on the surface. In addition, the spectral feature at ca. 1442 cm<sup>-1</sup> related to the carbonates (CO<sub>3</sub><sup>2-</sup>) decreased in intensity, while the absorption at higher (1700–1500 cm<sup>-1</sup>) and lower (1300–1150 cm<sup>-1</sup>) wavenumbers increased. These spectral regions are attributed to the bicarbonate C=O stretching vibrations of HCO<sub>3</sub><sup>-</sup>,<sup>34,35</sup> which may be the result of bicarbonate formation during carbonate protonation. The IR band of the asymmetric vibration of physisorbed CO<sub>2</sub> near 2350 cm<sup>-1</sup> grows slightly during irradiation; concomitantly, a very weak peak of adsorbed carbon monoxide (2148 cm<sup>-1</sup>) appears. All these observed spectral changes are amplified with irradiation time. However,

alterations in the spectral region of the C–H stretching vibration (3000–2800  $\text{cm}^{-1}$ ) differ during the photoprocess (Figure 10): first, C–H stretching bands appear after 30 min of irradiation (spectrum 1), followed by their disappearance after a longer irradiation time (spectrum 2), likely due to the formation of new CH-containing reaction products (probably hydrocarbons) that readily desorb owing to weak binding to the surface.

Evidently, some of the products formed are weakly adsorbed on the surface and so are mainly released and detected in the gas phase. Accordingly, it was imperative to examine the hydrophilicity of the surface of the barium bismuthate photocatalyst and possible photoinduced changes to the surface energy behavior during the heterogeneous photoreaction.

The initial hydrophilic state of the barium bismuthate was characterized by the water contact angle technique (WCA); initially the WCA was  $35.0 \pm 0.5$  degrees. WCAs less than 40 degrees are typical of high-energy surfaces in air, as occurs on a metal-oxide surface. Note that IR and XPS spectroscopic results of the surface composition indicated the presence of strongly bound surface water and carbonate species. Undoubtedly, the presence of such surface species may reduce the WCA, and consequently the surface free energy (SFE).

The mean WCA for the irradiated bismuthate surface decreased to  $26.0 \pm 0.5$  degrees subsequent to irradiation of the bismuthate sample for 2 hrs, which infers that band-to-band photoexcitation of the barium bismuthate leads to an increase of surface hydrophilicity (decrease in WCA) and hence to an increase of surface free energy. Recall that IR spectra of the sample showed that upon irradiation the physisorbed water molecules and carbonate species are removed from the surface, and thus contribute to the increase in SFE. Evidently, adsorption of substances having polar groups and high surface tension (e.g., water<sup>36</sup>) reduces the excess surface energy, and thus facilitates the supply of polar reagent molecules during the photoreduction of  $\text{CO}_2$  in the liquid and gaseous phases, and the displacement of less polar molecules (e.g., reaction products such as alkanes) from the surface as observed when carrying out the photoreduction of  $\text{CO}_2$  on the barium bismuthate surface. Such occurrences are of great practical importance for solving the problem of isolating reaction products from the reaction mixture, especially when carrying out liquid-phase photocatalytic processes.

Summarizing all the experimental data presented above suggests additional details into the mechanism of the photocatalytic reduction of carbon dioxide on the surface of the  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  photocatalyst in the IR cell. At first, carbon dioxide molecules from the gas phase are readily adsorbed on the surface, mostly in the form of carbonate functions (Figure S3). Photoexcitation of the sample in its *intrinsic* absorption region then leads to the formation of electron/hole photocarrier pairs (Figure 8). Photoelectrons are subsequently consumed (Figure 10) by the photoreduction of surface carbonates with formation of such products as carbon monoxide and hydrocarbons. Owing to the photoinduced increase in surface free energy (increased hydrophilicity of the surface), the non-polar alkanes formed are then easily removed from the surface of the barium bismuthate.

Although experimental results on the photoelectrochemical reduction of  $\text{CO}_2$  over the  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  surface obtained in the liquid phase and in the gaseous phase reactions show some differences in the nature of the reaction products, they do share some common events. Moreover, results confirm the relative location of the energy bands of the barium bismuthate

$\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  with respect to the redox potentials of the half-reactions implicating reduction of  $\text{CO}_2$  (Figure 8).

As an additional test to assess the activity (or lack thereof) of the barium bismuthate, the photodegradation of phenol was also investigated in an aqueous suspension of the as-synthesized metal-oxide photocatalyst sample in a batch-type reactor, as phenol is often used as an ideal substrate to examine the photoactivity of potential metal-oxide photocatalysts. The time course of the concentration of phenol in the aqueous suspension under irradiation for more than 6 hrs is displayed in Figure S7. Within experimental error, the  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  bismuthate had no effect on the oxidative decomposition of phenol when photoexcited in its *intrinsic* absorption region (ca. 550 nm) in the batch reactor with light at  $\lambda > 300$  nm.

### 3. Experimental

#### 3.1. Synthesis and characterization of the barium bismuthates

The novel barium bismuthate was prepared via a solid-state synthesis. For this purpose, two precursors, barium nitrate  $\text{BaNO}_3$  ( $\geq 99.5$  % purity; ACROS Chemicals) and bismuth(III) oxide ( $\text{Bi}_2\text{O}_3$ ,  $\geq 99.5$  % purity; ACROS Chemicals) were mixed in a ratio corresponding to 15.0 mol.% on a phase diagram. The mixture was then carefully ground in an agate mortar for 10 min in the presence of absolute ethanol (purity  $\geq 99.8$  % (GC), Vekton). The mixture was subsequently heated in two stages: during the first stage, barium nitrate was converted to barium oxide on heating at 650 °C for 12 hrs in air; in the second stage, formation of the single-phase barium bismuthate was achieved upon heating at 750 °C for at least 72 hrs also in air, followed by intermediate grinding and pressing of the reaction mixture every 10–12 hrs. For more detailed stages of the formation of barium bismuthate are given in the Supplementary Information and the corresponding text.

The phase composition of the bismuthate was examined by X-ray diffraction (XRD) and by Raman spectroscopy. Powdered diffraction data of the  $\text{Ba}_x\text{Bi}_y\text{O}_{(2x+3y)/2}$  were collected at ambient temperature using a Bruker D8 ADVANCE powder diffractometer with  $\text{CuK}\alpha$  radiation and linear VANTEC detector, following which the data were refined by the Rietveld method. The  $2\theta$  data collecting interval was 0.016 degrees and the collecting time was 1 s. Rietveld refinement was performed using the program TOPAS 4.2.<sup>37</sup> Raman spectra were recorded in the 80–1525  $\text{cm}^{-1}$  spectral regions at ambient temperature using a SENTERRA Raman spectrophotometer (Bruker; resolution, 2  $\text{cm}^{-1}$ ; laser excitation wavelength, 785 nm; laser beam power, 1 mW).

The morphology of the sample was determined by Scanning Electron Microscopy (SEM; TESCAN, Czech Republic; acceleration voltage, 20 kV). The elemental composition and its distribution in the as-synthesized barium bismuthate sample were established by Energy Dispersive X-ray spectroscopy (EDX; X-Max<sup>N</sup>, Oxford Instruments, UK). The specific surface area of the sample pretreated at 350 °C for 6 hrs was determined by the BET method using a Quadrasorb SI surface area analyzer ( $\text{N}_2$  adsorption).

The elemental composition of the surface and the position of the valence band (VB) were determined by X-ray Photoelectron Spectroscopy (XPS) using a Thermo Fisher Scientific Escalab 250Xi spectrophotometer (Al  $\text{K}\alpha$  radiation, 1486.6 eV; spectral resolution, 0.5 eV); the reference carbon line  $\text{C}_{1s}$  of a C–C bond was taken at a binding energy (BE) of 284.8 eV.<sup>38</sup>

Diffuse reflectance spectra, as  $R(\lambda)$ , were recorded in the 375–775 nm spectral range under ambient conditions on a Cary 5000 UV/Vis/NIR spectrophotometer equipped with a DRA 2500 external

diffuse reflectance accessory; optical grade BaSO<sub>4</sub> powder was the reference standard.

The hydrophilic properties of barium bismuthate were ascertained in the dark and under irradiation. The powdered sample was pressed into a self-supported pellet with dimensions 40/40/2 mm (width/height/thickness) using a hydraulic press. Surface hydrophilicity was characterized by determining the water contact angles (WCA) using a Theta Lite Optical Tensiometer (Biolin Scientific, Finland). To obtain greater reproducibility, the water contact angles were measured no less than six times after each manipulation; the average WCA value is reported. The photoinduced surface hydrophilicity of the barium bismuthate sample was ascertained by irradiating with light of various spectral compositions under stationary ambient conditions (temperature: +20 °C, relative humidity: *ca.* 50 %). For this purpose, a 150-W Xenon lamp (OSRAM, light irradiance, 7.3 mW cm<sup>-2</sup>) was used; total exposure time was 2 hrs.

### 3.2. Photoactivity of the BaBi<sub>2</sub>O<sub>4</sub>-type bismuthate

**3.2.1. Photoelectrochemical CO<sub>2</sub> reduction from aqueous solutions.** The photocatalytic activity of the as-synthesized barium bismuthate was evaluated via the photoelectrochemical reduction of CO<sub>2</sub>, which was carried out in a 100-mL, two compartment photoelectrochemical (PEC) cell used in the wired configuration with anatase TiO<sub>2</sub> as the photoanode and barium bismuthate as the photocathode separated by a proton-permeable membrane (DuPont™ Nafion® N-424). The electrical connection between the photoanode and photocathode was established by a copper wire. Both electrodes were irradiated by light from the 150-W Xenon lamp; the applied potential between the electrodes was 100 mV. A schematic of the photoelectrochemical (PEC) cell is illustrated in Figure S6.

Photoreduction of CO<sub>2</sub> occurred in the photocathode compartment enclosed by a quartz window. The compartment was first filled with a 0.5 M KHCO<sub>3</sub> aqueous solution, followed by purging the solution with gaseous carbon dioxide for 1 hr to saturate the solution with CO<sub>2</sub> and to remove oxygen from the electrolyte prior to irradiation. The photoanode compartment was also enclosed by a quartz window. Photooxidation of ammonium oxalate, (NH<sub>4</sub>)<sub>2</sub>C<sub>2</sub>O<sub>4</sub>, was chosen as the counter reaction occurring in the photoanode compartment; the electrolyte consisted of an equimolar aqueous solution of 0.2 M K<sub>2</sub>SO<sub>4</sub> and 0.2 M (NH<sub>4</sub>)<sub>2</sub>C<sub>2</sub>O<sub>4</sub>.

Preparation of the photocathode with the as-synthesized barium bismuthate consisted of compressing the powder using a hydraulic press into a pellet with dimensions of 21/31/2 mm (width/height/thickness). A silver-based conductive paste was applied to one side of this pellet, following which a copper wire was soldered to it and then coated with epoxy for electrical insulation. The photocathode so prepared provided only contact between the barium bismuthate pellet and the electrolyte.

The photoanode consisted of a thin film of anatase TiO<sub>2</sub> deposited on an FTO glass (25 x 25 mm, industrial glass; sheet resistance, < 100 Ω sq<sup>-1</sup>) using a sol-gel method and a two-step dip-coating technique (KSV Nima dip coater). The TiO<sub>2</sub> sol was prepared by mixing titanium isopropoxide (9 ml, 97 %, Sigma Aldrich), isopropyl alcohol (100 ml, ≥ 99.0 %, Vekton), and citric acid (18 g, chemical grade, Vekton) as the starting material, as the solvent, and as the stabilizer, respectively. In the first stage, a dense thin film was formed by a 5-fold immersion at a withdrawal velocity of 10 mm min<sup>-1</sup> with a 5-min dry air between each immersion, after which the FTO substrate was immersed into the same sol at a

withdrawal velocity of 50 mm min<sup>-1</sup> five more times. Subsequently, the coating was annealed at 500 °C for 6 hrs in air at a heating/cooling rate of 1 deg min<sup>-1</sup>. To further develop the electrode surface, a rough film was formed on top of the dense film by 5-fold immersions at withdrawal velocities of 50 mm min<sup>-1</sup> and 100 mm min<sup>-1</sup> with heating to 200 °C in air between immersions. Finally, the coating was annealed at 500 °C for 6 hrs in air at a heating/cooling rate of 1 deg min<sup>-1</sup>. The uncoated corner of the substrate was connected with a copper wire, which was isolated from the solution with sealing rings (Figure S1).

Liquid samples from the photocathode compartment of the PEC cell were analyzed chromatographically using a Chromatec Crystal 5000 gas chromatograph equipped with a 3 m x 2 mm HayeSep R 80/100 column and a methanator; helium was the carrier gas. The gas flow rate was 25 mL min<sup>-1</sup>. The temperatures of the evaporator, methanator, and flame-ionization detector were 200 °C, 325 °C, and 200 °C, respectively. The temperature of the starting column (40 °C) was increased to 200 °C at a heating rate of 20 degrees min<sup>-1</sup>. Before analyzing the reaction probes, chromatograms of some known alcohols and hydrocarbons were obtained to determine possible reaction products (Figure S2). The retention times of these products from the chromatographic column were determined under otherwise identical experimental conditions. Calibration curves for all the substances tested were used to determine the respective concentrations of products.

**3.2.2. FTIR spectroscopic study of photoreduction of CO<sub>2</sub> in the gas phase.** The stainless-steel cell used to examine the infrared spectra of the adsorbed species in the transmission mode was also used in carrying out the spectroscopic study of the photocatalytic reduction of CO<sub>2</sub> gas over barium bismuthate. The cell's construction and operating mode have been described in detail elsewhere by Bulanin and coworkers.<sup>39</sup>

Prior to the photoinduced experiment, a powdered barium bismuthate sample was pressed into a thin self-supported pellet (thickness, 0.1 mm; specific weight, 9.4 g cm<sup>-3</sup>), which was then annealed at 350 °C (620 K) in vacuum (10<sup>-4</sup> Torr) for 2 hrs and then in oxygen for 2 hrs followed by cooling to ambient temperature and thorough evacuation of the sample. Subsequently, gaseous carbon dioxide (10 Torr in equilibrium) was introduced on the barium bismuthate sample at ambient temperature, followed by irradiating the sample with the 150-W Xenon lamp (irradiance, 7.3 mW cm<sup>-2</sup>) for 100 min.

During the experiment, IR spectra of the sample and of the gas phase in the sample-containing volume were recorded in the 1000–3800 cm<sup>-1</sup> spectral region at ambient temperature using a Thermo Scientific Nicolet iS50 FTIR spectrophotometer equipped with a DTGS detector; between 600 and 2000 scans were collected to obtain the IR spectra at a spectral resolution of 6 cm<sup>-1</sup>.

**3.2.3. Liquid-phase photodegradation of phenol.** To assess the photocatalytic visible-light-activity (or lack thereof) of the bismuthate sample we used the photodecomposition of phenol in an aqueous suspension in a batch-type reactor equipped with a quartz window for UV irradiation under ambient conditions. Before irradiation, the aqueous suspension (photocatalyst loading, 1.0 g L<sup>-1</sup>; pH, 7.0; volume, 300 mL) was treated in an ultrasonic processor for 10 min followed by addition of 100 ppm of phenol (Aldrich; purity, 99.5 %; 1.06 mM) and then magnetically stirred for 1 hr under dark conditions to achieve an adsorption-desorption equilibrium. The selected initial concentration of phenol ensured that the reaction rate was independent of concentration. The light

source was the 150-W Xenon lamp (OSRAM); an optical cutoff filter removed UV wavelengths below 300 nm (light irradiance, 7 mW cm<sup>-2</sup>) so as to prevent direct photolysis of phenol through light absorption by the substrate.

To determine the time course of the concentration of phenol, aliquot samples were collected at given intervals and then analyzed by HPLC analysis performed using a 1260 Infinity liquid chromatograph equipped with a UV/Vis detector and a C18 column (Agilent Technologies). Prior to the chromatographic analysis, samples were filtered through a 0.2 μm Minisart filter to remove any solid particles. The mobile phase was a 50/50 v/v mixture of methanol/water; the detection wavelength was 210 nm and the bandwidth was 4 nm.

The initial rate of the photocatalytic reaction, often taken as a characteristic of the activity of a photocatalyst, in the present case the as-synthesized barium bismuthate, was determined from the kinetic approximation:

$$C(t) = C_0 \exp(-kt) \quad (2)$$

so that

$$dC/dt_{(t \rightarrow 0)} = -kC_0 \quad (3)$$

where  $k$  is the apparent *quasi*-first-order rate constant.

#### 4. Computational specifics

Periodic DFT calculations were performed using the GGA Perdew-Burke-Ernzerhof (PBE) density functional<sup>40,41</sup> as implemented in the ABINIT 6.8.3 program.<sup>42</sup> A basis set in the form of the Troullier-Martins norm-conserving pseudopotentials<sup>43</sup> was employed with a kinetic energy cutoff of 30 Hartree. The  $R$ -3 $m$  symmetry of the material's crystal lattice determined from the XRD analysis was enforced in all calculations. The Brillouin Zone (BZ) was sampled over the automatically generated  $\Gamma$ -point-centered  $8 \times 8 \times 8$  Monkhorst-Pack grid of  $k$ -points.<sup>44</sup> The electronic band structure was computed at 81  $k$ -points along the  $\Gamma$ -F-L-L1-Z high symmetry path of the trigonal BZ. The default total energy convergence criterion of  $1.0 \times 10^{-8}$  Hartree was applied. The electronic band structure and density of states were plotted using the Gnuplot 5.2 software package.<sup>45</sup> Optical absorption spectra were computed based on the Bethe-Salpeter Equation.<sup>46</sup>

#### 5. Concluding remarks

This study reports on the synthesis and comprehensive characterization of a most promising semiconductor photocatalyst of the BaBi<sub>2</sub>O<sub>4</sub> class, which following the Rietveld refinement can be described as Ba<sub>1.264(4)</sub>Bi<sub>1.971(4)</sub>O<sub>4</sub>. Various experimental techniques (XPS, DRS, SEM, and EDX) were brought to bear on its characterization, and together with a computational approach (DFT) the relevant energy band structure of this novel material was determined. The **energies** of the valence band and the conduction band were +1.14 eV and -1.12 eV, respectively; the indirect bandgap of this bismuthate semiconductor was  $E_g = 2.26$  eV (absorption edge  $\approx 550$  nm). Accordingly, this bismuthate system is a potentially viable visible-light-active photocatalyst. Both **energies** are rather high in comparison to those for most known photocatalysts. However, such an anomalous energy arrangement of the conduction band opens up unique possibilities for using this bismuthate for the photocatalytic reduction of a currently controversial greenhouse gas, carbon dioxide, while oxidative half-

reactions appear rather unlikely as attested by the lack of photoinduced oxidation of phenol. The photoreduction of CO<sub>2</sub> over the Ba<sub>1.264(4)</sub>Bi<sub>1.971(4)</sub>O<sub>4</sub> surface was examined photoelectrochemically in a PEC cell in aqueous media and spectroscopically using an IR cell reactor for the photoreduction in the gas phase. Chromatographic analyses of the reaction products revealed the main products differed somewhat: a mixture of carbon monoxide and alkanes from adsorbed CO<sub>2</sub> in the gas/solid system versus a mixture of alcohols and alkanes from the liquid/solid system. No attempts were made in the present study to optimize the experimental conditions.

#### Acknowledgements

The current research was kindly funded by a grant from the Russian Science Foundation (project No. 19-73-10013). R.K., A.V.R., V.K.R. and T.V.B. acknowledge financial support from Saint-Petersburg State University (Pure ID 39054581). A.V.R. thanks the Russian Foundation for Basic Research for a Grant No. 18-03-00855 that supported studies into the photoinduced hydrophilicity of the bismuthate. The authors are further grateful to the staff of the Khabarovsk Innovation and Analytical Center of the Yu. A. Kosygin Institute of Tectonics and Geophysics of the Far Eastern Branch of the Russian Academy of Sciences, and the Resource Centers of the Research Park at the Saint-Petersburg State University: (i) the Center for Diagnostics of Functional Materials for Medicine, Pharmacology and Nanoelectronics, (ii) the Center for Physical Methods of Surface Investigation, (iii) the Center for Optical and Laser Materials Research, together with the laboratories of (iv) Nanotechnology and (v) Nanophotonics for their valuable assistance in carrying out the research and in providing the needed equipment. One of us (N.S.) is grateful to Prof. Angelo Albini and the staff of the PhotoGreen Laboratory at the University of Pavia, Italy, for their continued hospitality.

#### Conflicts of interest

There are no conflicts to declare.

#### ORCID of all authors


D.S. Shtarev	0000-0002-1274-0183
A.V. Shtareva	0000-0003-0011-7578
R. Kevorkyants	0000-0002-2592-8353
A.V. Rudakova	0000-0002-6223-9223
M.S. Molokeyev	0000-0002-8297-0945
T.V. Bakiev	0000-0001-6325-3767
K.M. Bulanin	0000-0002-5715-8242
V.K. Ryabchuk	0000-0001-5302-2666
N. Serpone	0000-0003-0236-9795

#### Notes and references

- 1 L.V. Bora and R.K. Mewada, *Renew. Sustain. Energy Rev.* 2017, **76**, 1393–1421.
- 2 X. Wang, F. Wang, Y. Sang, and H. Liu, *Adv. Energy Mater.* 2017, **7**, 1700473.
- 3 T. Tatarchuk, A. Peter, B. Al-Najar, J. Vijaya, and M. Bououdina, in *Nanotechnology in Environmental Science*, C.M. Hussain and A.K. Mishra, Eds. Wiley-VCH Verlag GmbH

- & Co. KGaA, Weinheim, Germany, 2018, chapter 8, pp 209– 32 292.
- 4 X. Li, J. Yu, M. Jaroniec, and X. Chen, *Chem. Rev.* 2019, **119**, 33 3962–4179.
- 5 D.S. Shtarev, A.V. Shtareva, V.K. Ryabchuk, A.V. Rudakova, 34 P.D. Murzin, M.S. Molokeev, A.V. Koroleva, A.I. Blokh, and 35 N. Serpone, *Catal. Today* 2020, **340**, 70–85.
- 6 D.S. Shtarev, A.I. Blokh, E.O. Nashchochin, and A.V. 36 Shtareva, *Opt. Quant. Electron.* 2018, **50**, 228.
- 7 D.S. Shtarev, A.V. Shtareva, V.K. Ryabchuk, A.V. Rudakova, 37 and N. Serpone, *ChemCatChem* 2019, **11**, 3534–3541.
- 8 Y.C. Yang, X.Z. Wang, and J. Qu, *Appl. Mech. Mater.* 2014, 38 **522-524**, 411–415.
- 9 W. Zhou and X. Yu, *Desalin. Water Treat.* 2011, **30**, 295–299. 38
- 10 Z. Shan, Y. Xia, Y. Yang, H. Ding, and F. Huang, *Mater. Lett.* 39 **2009**, **63**, 75–77.
- 11 Y. Obukuro, S. Matsushima, K. Obata, T. Suzuki, M. Arai, E. 40 Asato, Y. Okuyama, N. Matsunaga, and G. Sakai, *J. Alloys* **40** *Comp.* 2016, **658**, 139–146.
- 12 X. Hu, C. Hu, and J. Qu, *Appl. Catal. B: Environ.* 2006, **69**, 17– 41 23.
- 13 C. Hu, X. Hu, J. Guo, and J. Qu, *Environ. Sci. Technol.* 2006, 42 **40**, 5508–5513.
- 14 S.-H. Lee, W.-H. Jung, J.-H. Sohn, J.-H. Lee, and S.-H. Cho, *J. 43* *Appl. Phys.* 1999, **86**, 6351– 6354.
- 15 J. Tang, Z. Zou, and J. Ye, *J. Phys. Chem. C* 2007, **111**, 44 **12779–12785**.
- 16 T. Hatakeyama, S. Takeda, F. Ishikawa, A. Ohmura, A. 45 Nakayama, Y. Yamada, A. Matsushita, and J. Yea, *J. Ceram. Soc. Jpn.*, 2010, **118**, 91–95.
- 17 M. Khraisheh, A. Khazndar, and M.A. Al-Ghouti, *Int. J. Energy 46* *Res.* 2015, **39**, 1142–1152.
- 18 J. Ge, W.-J. Yin, and Y. Yan, *Chem. Mater.* 2018, **30**, 1017–1031. 45
- 19 B. Yan, M. Jansen, and C. Felser, *Nature Phys.* 2013, **9**, 709–711.
- 20 N.C. Plumb, D.J. Gawryluk, Y. Wang, Z. Ristić, J. Park, B.Q. Lv, Z. 46 Wang, C.E. Matt, N. Xu, T. Shang, K. Conder, J. Mesot, S. Johnston, M. Shi, and M. Radović, *Phys. Rev. Lett.* 2016, **117**, 037002.
- 21 B. Weng, Z. Xiao, W. Meng, C.R. Grice, T. Poudel, X. Deng, and Y. 47 Yan, *Adv. Energy Mater.* 2017, **7**, 1602260.
- 22 Y.-Y. Wang, G.F. Feng, T.E. Sutto, and Z. Shao, *Phys. Rev. B: 48* *Condens. Matter Mater. Phys.*, 1991, **44**, 7098–7101.
- 23 H. Namatame, A. Fujimori, H. Takagi, S. Uchida, F.M.F. de Groot, 49 and J.C. Fuggle, *Phys. Rev. B: Condens. Matter Mater. Phys.* 1993, **48**, 16917–16925.
- 24 S.N. Habisreutinger, L. Schmidt-Mende, and J.K. Stolarczyk, 50 *Angew. Chem. Int. Edn.* 2013, **52**, 7372–7408.
- 25 Y. Matsumoto, *J. Solid State Chem.* **1996**, **126**, 227–234.
- 26 P. Conflant, J.C. Boivin, G. Nowogrocki, and D. Thomas, *Solid 51* *State Ionics* 1983, **9-10** (Part 2), 925–928.
- 27 Relevant crystallographic data have been deposited in the 52 Cambridge Crystallographic Data Center (CCDC # 1962724) and can be downloaded from their website: [http://www.ccdc.cam.ac.uk/data\\_request/cif](http://www.ccdc.cam.ac.uk/data_request/cif)
- 28 V.N. Denisov, A.N. Ivlev, A.S. Lipin, B.N. Mavrin, and V.G. Orlov, 53 *J. Phys. Cond. Matter* 1999, **23**, 4967–4978.
- 29 D. de Waal, K.-J. Range, M. Königstein, and W. Kiefer, *J. Raman 54* *Spectros.* 1998, **29**, 109–113.
- 30 W. Luo, J. Tang, Z. Zou, and J. Ye, *J. Alloys Comp.* 2008, **455**, 346–352.
- 31 R.J. Betsch and W.B. White, *Spectrochim. Acta Part A: Molec. 55* *Spectros.* 1978, **34**, 505–514.
- F.D. Hardcastle and I.E. Wachs, *J. Solid State Chem.* 1992, **97**, 319–331.
- S.A. Chambers, T. Droubay, T.C. Kaspar, M. Gutowski, and M. 56 van Schilfhaarde, *Surf. Sci.* 2004, **554**, 81–89.
- F.A. Miller and C.H. Wilkins, *Anal. Chem.* 1952, **24**, 1253–1294.
- G. Socrates, *Infrared and Raman characteristic group 57* frequencies. Tables and Charts, John Wiley & Sons, Chichester, UK, 2001.
- Dortmund Data Bank; see <http://www.ddbst.com/> (accessed 58 October 2019).
- Bruker AXS TOPAS V4: General profile and structure analysis 59 software for powder diffraction data. – User’s Manual. Bruker AXS, Karlsruhe, Germany. 2008.
- NIST X-ray Photoelectron Spectroscopy Database; see 60 <https://www.srdata.nist.gov/xps/> (accessed October 2019).
- K.M. Bulanin, D.W. Bahnemann, and A.V. Rudakova, *Rev. Sci. 61* *Instrum.* 2019, **90**, 105113.
- J.P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* 1996, 62 **77**, 3865–3868.
- J.P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* 1997, 63 **78**, 1396–1396.
- X. Gonze, B. Amadon, P.M. Anglade, J.-M. Beuken, F. Bottin, P. 64 Boulanger, F. Bruneval, D. Caliste, R. Caracas, M. Cote, T. Deutsch, L. Genovese, Ph. Ghosez, M. Giantomassi, S. Goedecker, D. Hamann, P. Hermet, F. Jollet, G. Jomard, S. Leroux, M. Mancini, S. Mazevet, M.J.T. Oliveira, G. Onida, Y. Pouillon, T. Rangel, G.-M. Rignanese, D. Sangalli, R. Shaltaf, M. Torrent, M.J. Verstraete, G. Zerah, and J.W. Zwanziger, *Comput. 65* *Phys. Commun.* 2009, **180**, 2582–2615.
- N. Troullier and J.L. Martins, *Phys. Rev. B* 1991, **43**, 1993.
- H.J. Monkhorst and J.D. Pack, *Phys. Rev. B* 1976, **13**, 5188– 66 5192.
- T. Williams, C. Kelley, E.A. Merritt, C. Bersch, H.-B. Bröker, J. 67 Campbell, R. Cunningham, D. Denholm, G. Elber, R. Fearick, C. Grammes, L. Hart, L. Hecking, P. Juhász, T. Koenig, D. Kotz, E. Kubaitis, R. Lang, T. Lecomte, A. Lehmann, J. Lodewyck, A. Mai, B. Märkisch, P. Mikulík, D. Sebald, C. Steger, S. Takeno, T. Tkacik, J. van der Woude, J.R. van Zandt, A. Woo, and J. Zellner, *Gnuplot 5.2: An interactive plotting program*, 2018; see [http://www.gnuplot.info/docs\\_5.2/Gnuplot\\_5.2.pdf](http://www.gnuplot.info/docs_5.2/Gnuplot_5.2.pdf) (accessed 68 November 2019).
- E.E. Salpeter and H.A. Bethe, *Phys. Rev.* 1951, **84**, 1232–1242.

## Table of Contents entry

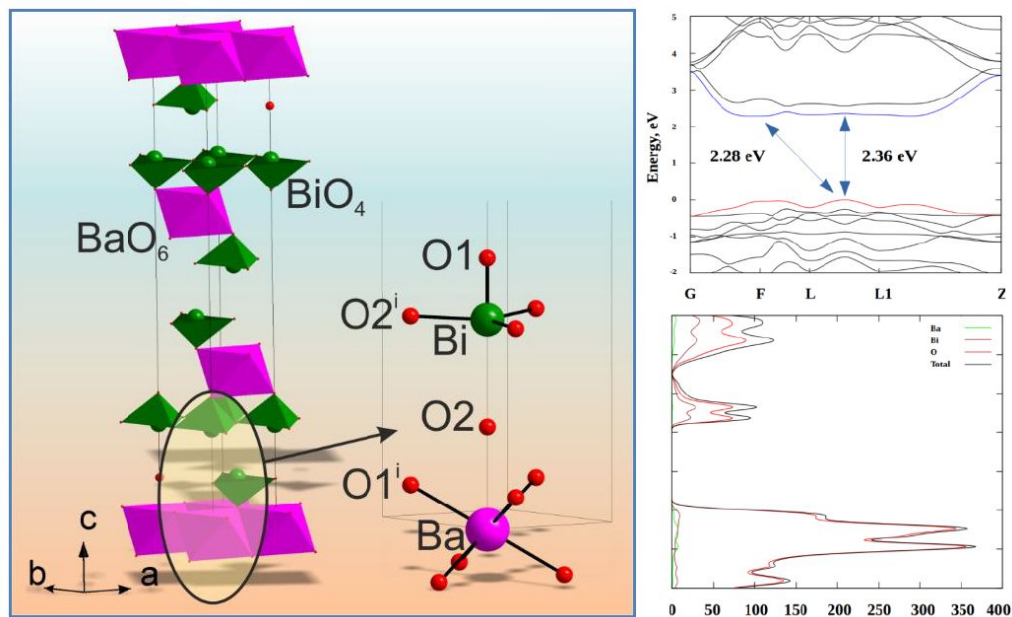

Crystal structure of the  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  perovskite-like system and associated electronic band structure and density of states.



January 28, 2020

## Supplementary Material

### Materials Synthesis, Characterization and DFT Calculations. The Visible-Light-Active Perovskite-like Barium Bismuthate ( $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$ ) Photocatalyst.

D.S. Shtarev,<sup>1,2</sup> A.V. Shtareva,<sup>1,2</sup> R. Kevorkyants,<sup>3</sup> A.V. Rudakova,<sup>3</sup> M.S. Molokeev,<sup>2,4,5</sup> T.V. Bakiev,<sup>3</sup> K.M. Bulanin,<sup>3,6</sup> V.K. Ryabchuk,<sup>3,6</sup> and N. Serpone<sup>7,\*</sup>

- <sup>1</sup> Yu. A. Kosygin Institute of Tectonics and Geophysics, Far Eastern branch of the Russian Academy of Sciences, 65 Kim Yu Chen Street, Khabarovsk, 680063 Russian Federation; emails: [shtarev@mail.ru](mailto:shtarev@mail.ru) and [avshhtareva@mail.ru](mailto:avshhtareva@mail.ru)
- <sup>2</sup> Far Eastern State Transport University, 47 Seryshev Street, Khabarovsk, 680021 Russian Federation; email: [msmolokeev@mail.ru](mailto:msmolokeev@mail.ru)
- <sup>3</sup> Saint-Petersburg State University, Laboratory "Photoactive Nanocomposite Materials", Ul'yanovskaya 1, Petergof, Saint-Petersburg, 198904, Russian Federation; emails: [ruslan.kevorkyants@gmail.com](mailto:ruslan.kevorkyants@gmail.com), [aida.rudakova@spbu.ru](mailto:aida.rudakova@spbu.ru), [tairbakiev@gmail.com](mailto:tairbakiev@gmail.com)
- <sup>4</sup> Kirensky Institute of Physics, Akademgorodok 50, bld. 38, Krasnoyarsk, 660036 Russian Federation
- <sup>5</sup> Siberian Federal University, 79 Svobodny pr., 660041 Krasnoyarsk, Russian Federation
- <sup>6</sup> Saint-Petersburg State University, Department of Photonics, Ul'yanovskaya 1, Petergof, Saint-Petersburg, 198904 Russian Federation; email: [v.ryabchuk@spbu.ru](mailto:v.ryabchuk@spbu.ru) and [k.bulanin@spbu.ru](mailto:k.bulanin@spbu.ru)
- <sup>7</sup> PhotoGreen Laboratory, Dipartimento di Chimica, Universita di Pavia, via Taramelli 12, Pavia 27100, Italia; email: [nick.serpone@unipv.it](mailto:nick.serpone@unipv.it)

\* Corresponding author: [nick.serpone@unipv.it](mailto:nick.serpone@unipv.it)


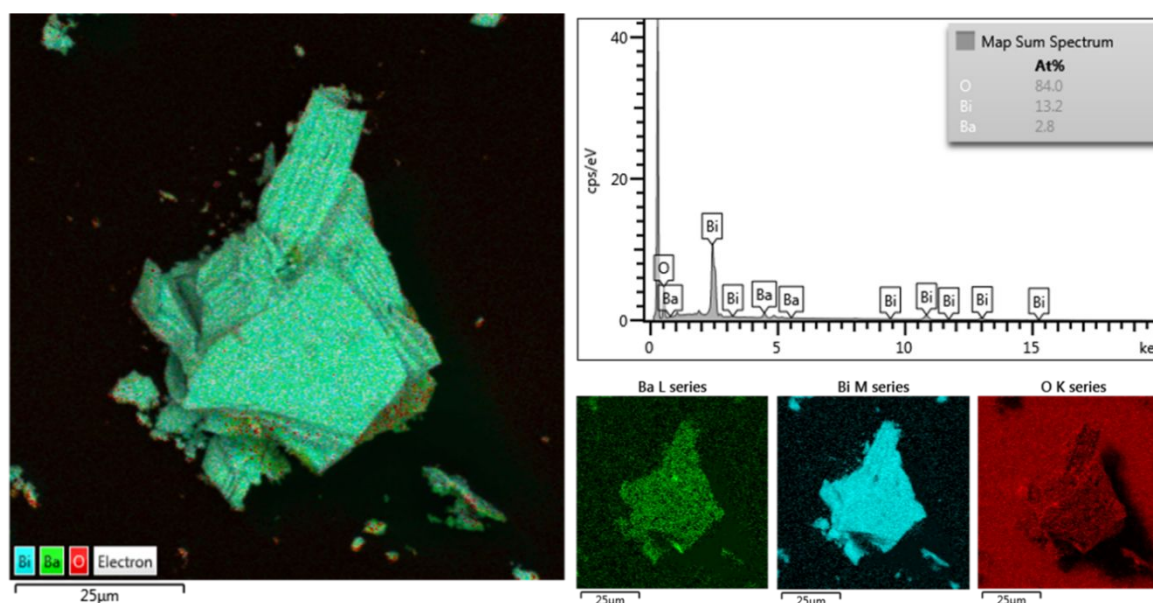



Figure S1. EDX spectrum and mapping of the elements of the barium bismuthate particle.

January 28, 2020

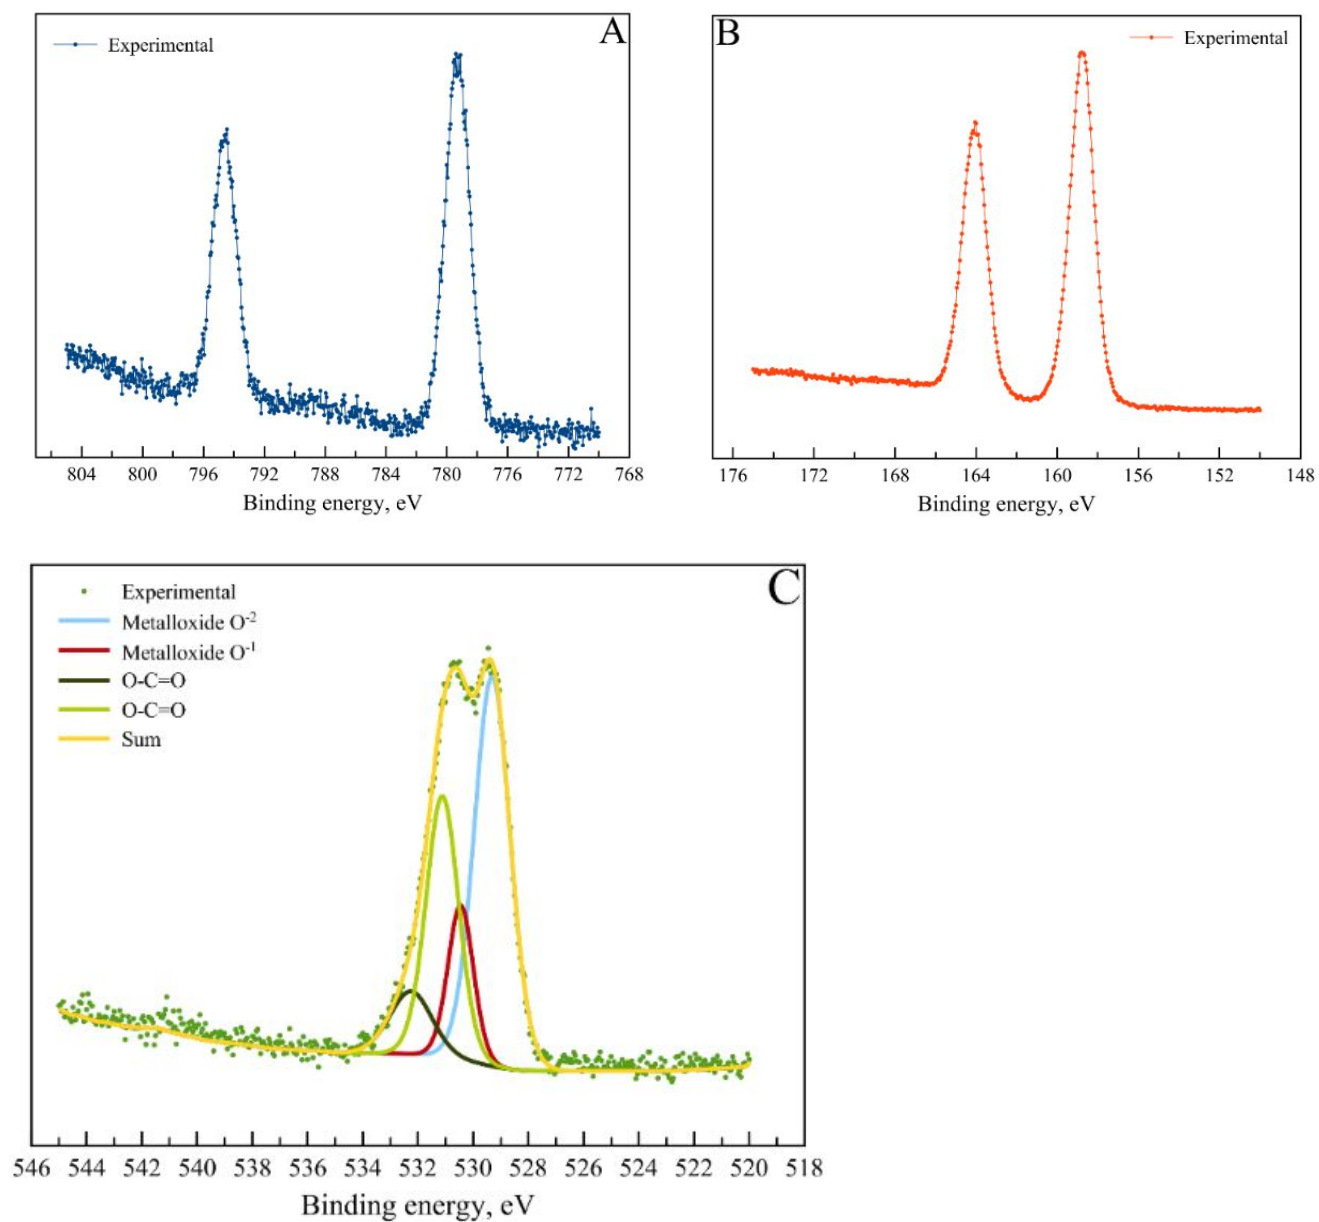



**Figure S2.** XPS spectra and deconvolution results of the synthesized barium bismuthate  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  sample in the  $\text{Ba}3d$  (A),  $\text{Bi}4f$  (B), and  $\text{O}1s$  (C) regions.

January 28, 2020

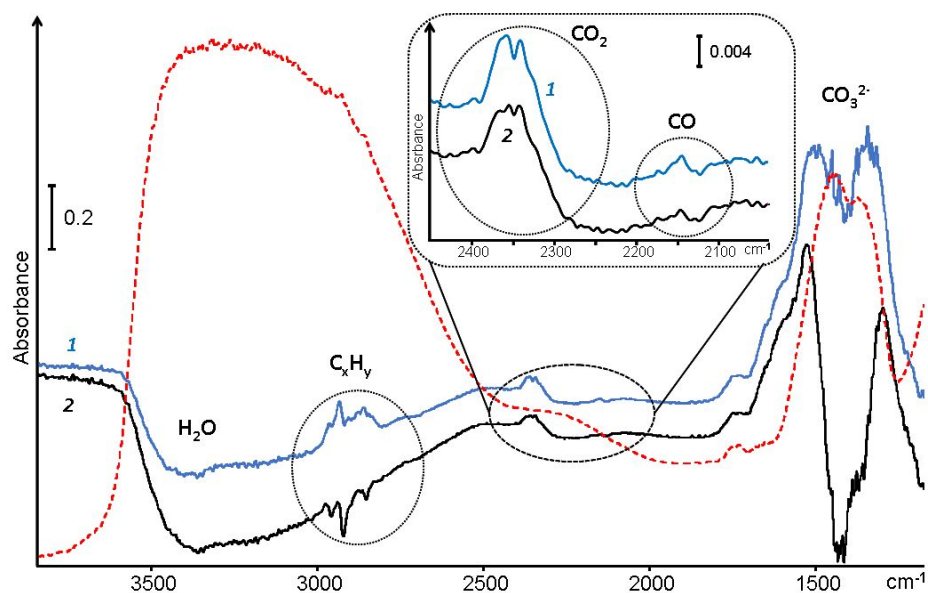


**Figure S3.** FTIR spectroscopic results of the photocatalytic reduction of  $\text{CO}_2$  on the  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  bismuthate particle surface in the gas/solid system: **1** (blue line) – difference spectrum of the sample irradiated for 30 min; **2** (black line) – difference spectrum of the sample irradiated for 100 min; **3** (red dotted line) – original spectrum of the barium bismuthate sample before the photo-experiment, as a reference. Difference spectra were obtained by subtraction of the spectrum of the sample after introduction of  $\text{CO}_2$  from the current spectrum. The inset shows an enlarged view of difference spectra **1** and **2** in the  $2450\text{--}2050\text{ cm}^{-1}$  spectral regions.

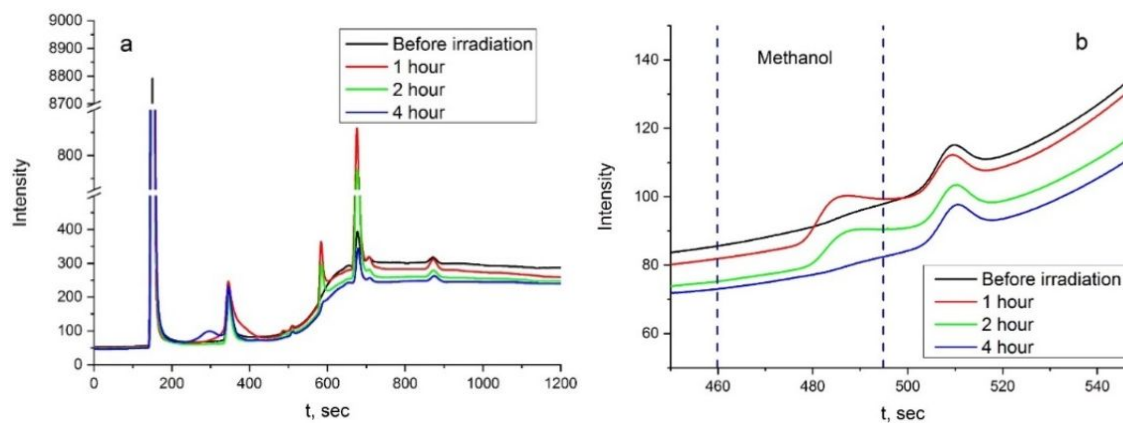

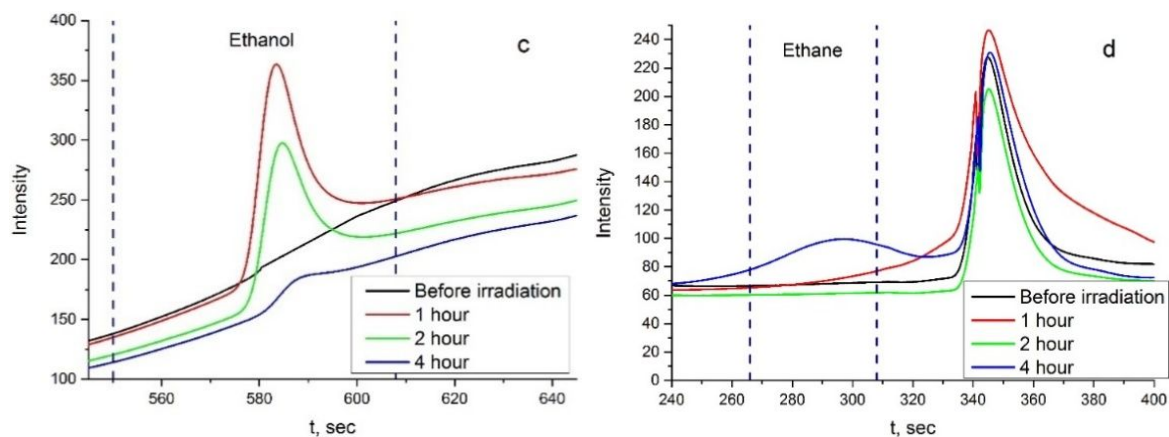


**Figure S4.** Results of chromatographic analyses from liquid aliquots taken from the photocathode compartment of the PEC cell before and during the photoelectrochemical reaction. (a) Overall view of the chromatograms of the liquid samples from the photocathode compartment of the PEC cell before irradiation (black) and after irradiation for 1 (red), 2 (green), and 4 (blue) hrs; (b)-(d) enlarged chromatograms in the retention areas of methanol (460–495 sec), ethanol (550–608 sec) and ethane (266–308 sec).

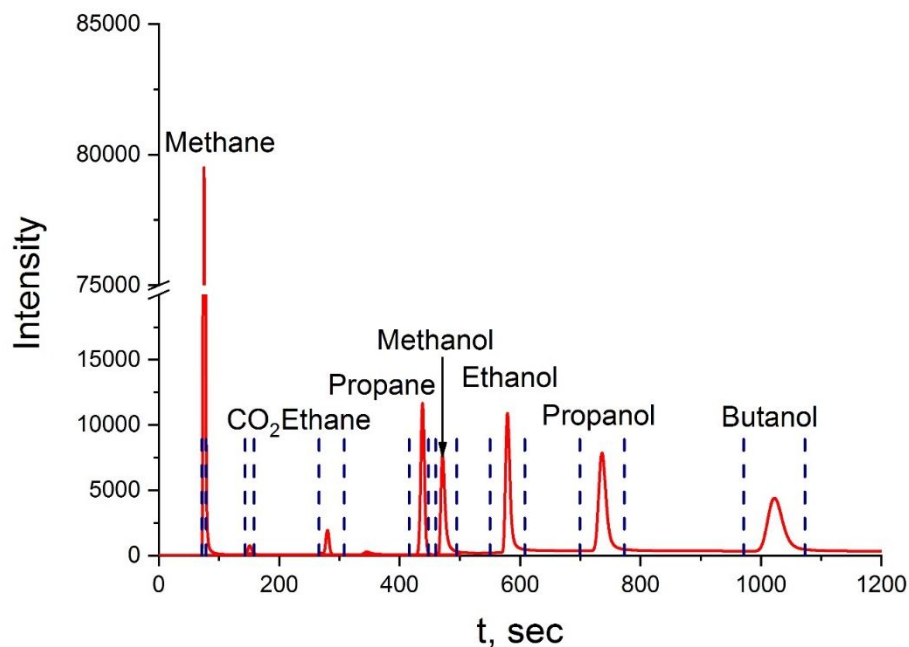


**Figure S5.** Chromatograms of possible products from the photoreduction of  $\text{CO}_2$  (red solid line); vertical blue dashed lines define the confidence intervals used for product identification within  $\pm 5\%$  of the retention time required for maximum product generation.

January 28, 2020

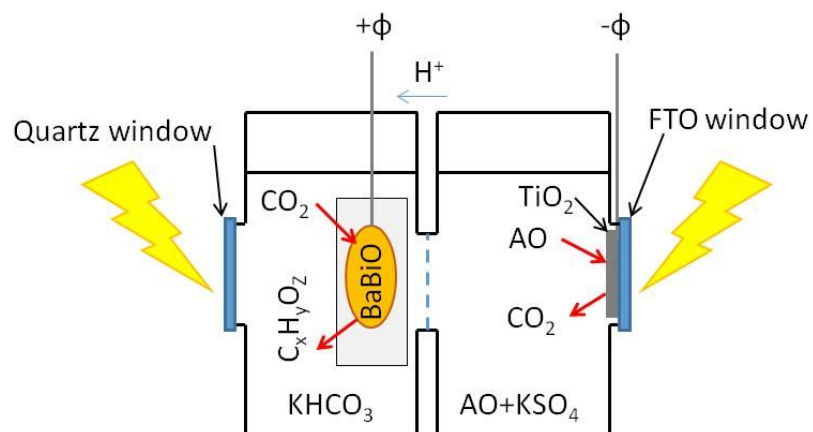

**Figure S6.** Scheme of the PEC cell for the photoelectrochemical reduction of  $\text{CO}_2$ ; AO is ammonium oxalate, and  $\text{C}_x\text{H}_y\text{O}_z$  denotes various products of the  $\text{CO}_2$  reduction.

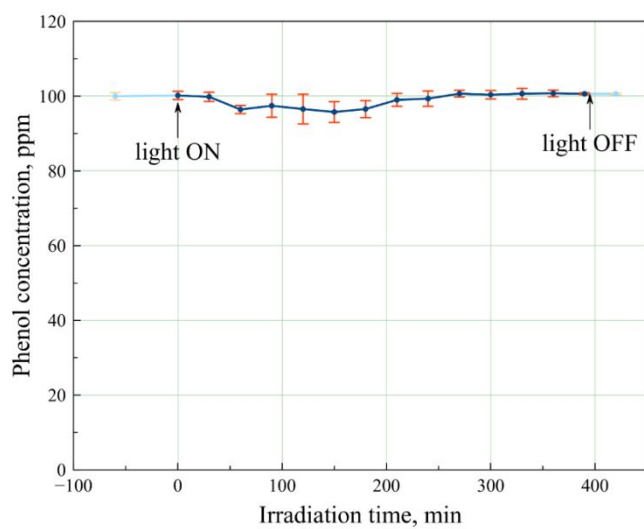

**Figure S7.** Time course of the concentration of phenol in aqueous media in the presence of  $\text{Ba}_{1.264(4)}\text{Bi}_{1.971(4)}\text{O}_4$  as a function of irradiation time.