

# Spin susceptibility of the two-orbital model within the cluster perturbation theory for Fe-based materials

S.V. Nikolaev · M.M. Korshunov

Received: date / Accepted: date

**Abstract** Cluster perturbation theory is used to calculate band structure, spectral functions, Fermi surface, and spin and charge susceptibilities for the two-orbital model of iron pnictides with the on-site multiorbital Hubbard interactions. Spin and charge susceptibility is calculated within the approximation combining the cluster perturbation theory for the self-energy corrections and the random-phase approximation (RPA) for the vertex renormalizations. Calculations for the small values of Hubbard repulsion  $U \leq 2$  confirm that the rigid band approximation and the RPA for the spin and charge susceptibility are suitable approaches for the case of weak interactions.

**Keywords** Fe-based superconductors · Mutiorbital models · Cluster perturbation theory

## 1 Introduction

Iron-based materials - pnictides and chalcogenides - represent a new class of unconventional superconductors with high transition temperatures [1–9]. While the mechanism of superconductivity is still a mystery, the main candidates are spin or orbital fluctuations. Except for the extreme hole and electron dopings, the Fermi surface (FS) consists of two or three hole pockets around the  $\Gamma = (0, 0)$  point and two electron pockets around the  $X = (\pi, 0)$  and  $Y = (0, \pi)$  point in the Brillouin zone, corresponding to the one iron per unit


cell. Different mechanisms of Cooper pairs formation result in the distinct superconducting gap symmetry and structure in Fe-based superconductors (FeBS) [8]. For example, spin fluctuation approach leads to the extended  $s_{\pm}$  state ( $s$ -wave gap that changes sign between hole and electron FSs) as the main instability [10–15], while orbital fluctuations promote the order parameter to have the sign-preserving  $s_{++}$  symmetry [16, 17].

Most approaches to the superconductivity theory in FeBS including spin fluctuations in the random-phase approximation (RPA) are solidly justified in the case of a weak interaction between electrons. Agreement between the experimental FS and the one theoretically calculated within density functional theory (DFT) as well as the smallness of the magnetic moment in most FeBS and absence of Mott insulating state even in the undoped materials assert that the interaction is weak. On the other hand, comparison of ARPES (angle-resolved photoemission spectroscopy) results and DFT bands shows the bandwidth reduction about two to three times [18], and the redistribution of spectral weight from the Drude peak to higher energies in optical conductivity of LaFePO BaFe<sub>2</sub>As<sub>2</sub> points out to the at least moderate electronic correlations [19]. While the use of hybrid methods like LDA+DMFT (local density approximation + dynamical mean-field theory) to treat electronic correlations allows to describe some physical properties of FeBS [20–23], nonlocal spin fluctuations are beyond these approaches. Thus it is hard to justify use of methods like LDA+DMFT to build up a theory of superconductivity where spin fluctuations are crucial [8]. Cluster extensions of DMFT, e.g., CDMFT (cellular DMFT) [24] and DCA (dynamical cluster approximation) [25–27], are numerically very expensive for the multiorbital systems. Here we use alternative approach called the cluster perturbation theory (CPT) [28, 29]. It relies on the

---

S.V. Nikolaev and M.M. Korshunov  
Kirensky Institute of Physics, Akademgorodok, Krasnoyarsk  
660036, Russia  
E-mail: mkor@iph.krasn.ru

Siberian Federal University, Svobodny Prospect 79, Krasnoyarsk 660041, Russia

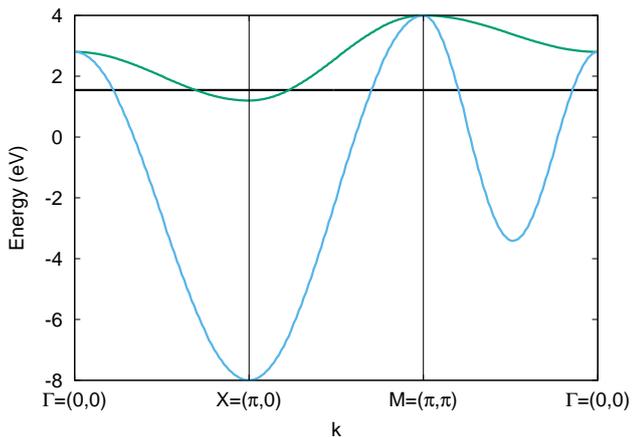

**Fig. 1** Band structure of model (1).

exact diagonalization of the small cluster to calculate a cluster Green's function. Then the intercluster hoppings and interactions are treated as perturbations. Such procedure allows to describe spin and charge fluctuations within the cluster exactly.


Here we use CPT to calculate spin susceptibilities for the simple two-orbital model of iron pnictides [30] with the on-site multiorbital Hubbard interactions. First, we calculate full Green's functions via CPT. Then susceptibilities are obtained within RPA with the bare polarization bubble composed of full CPT Green's functions. Since the susceptibility is the central part of the spin/charge fluctuation-driven Cooper pairing, this is the essential step towards the theory of superconductivity in FeBS.

## 2 Model and Methods

To preserve orbital content of the bands and still gain some simplicity, we study here the two-orbital tight-binding model from Ref. [30] with Hamiltonian

$$H_0 = \sum_{\mathbf{k}\sigma} \sum_{l'l'} [t_{ll'}(\mathbf{k}) + \epsilon_l \delta_{ll'}] d_{l\mathbf{k}\sigma}^\dagger d_{l'\mathbf{k}\sigma}, \quad (1)$$

where  $d_{l\mathbf{k}\sigma}^\dagger$  is the annihilation operator of a particle with momentum  $\mathbf{k}$ , spin  $\sigma$ , and orbital index  $l = 1, 2$  enumerating  $d_{xz}$  and  $d_{yz}$  orbitals. Later we use numerical values of hopping matrix elements  $t_{ll'}(\mathbf{k})$  and one-electron energies  $\epsilon_l$  from Ref. [30]. This model produce the band structure shown in Fig. 1 and the FS composed of one hole pocket around the  $\Gamma$  point and two electron pockets centered around  $X$  and  $Y$  points, see Fig. 2.

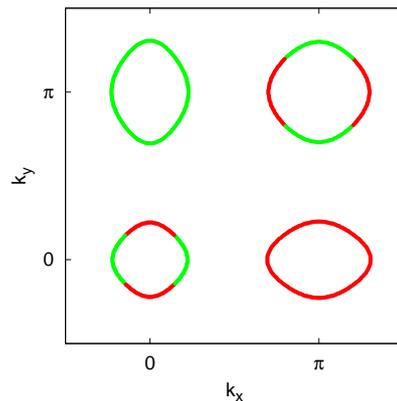

**Fig. 2** Fermi surface of model (1). Different colors indicate major orbital contribution (red -  $d_{xz}$ , green -  $d_{yz}$ ).

The general two-particle on-site interaction is given by the Hamiltonian [11, 12, 31, 32]:

$$\begin{aligned} H_{int} = & U \sum_{f,m} n_{fm\uparrow} n_{fm\downarrow} + U' \sum_{f,m<l} n_{fl} n_{fm} \\ & + J \sum_{f,m<l} \sum_{\sigma,\sigma'} d_{fl\sigma}^\dagger d_{fm\sigma'}^\dagger d_{fl\sigma'} d_{fm\sigma} \\ & + J' \sum_{f,m\neq l} d_{fl\uparrow}^\dagger d_{fl\downarrow}^\dagger d_{fm\downarrow} d_{fm\uparrow}. \end{aligned} \quad (2)$$

where  $n_{fm} = n_{fm\uparrow} + n_{fm\downarrow}$ ,  $n_{fm\sigma} = d_{fm\sigma}^\dagger d_{fm\sigma}$  is the number of particles operator at the site  $f$ ,  $U$  and  $U'$  are the intra- and interorbital Hubbard repulsion,  $J$  is the Hund's exchange, and  $J'$  is the so-called pair hopping. We restrict the number of interaction parameters by obeying the spin-rotational invariance:  $U' = U - 2J$  and  $J' = J$ .

### 2.1 CPT

We use the cluster perturbation theory [28, 29]. First step is the exact diagonalization of the small cluster. Here we choose 2x2 cluster of iron sites. Each site has 2 iron orbitals. The initial lattice is tiled by identical 2x2 clusters. Thus, the lattice transforms into a superlattice of clusters with a new translational order parameter which is an artificial origin. Here we use the averaging over two tilings which are discussed in framework of the norm-conserving cluster perturbation theory (NC-CPT) [33–35]. We treat the intercluster hoppings and interactions as perturbations.

In first step, we calculate the cluster Green's function  $G_{il,jm}^{(c)}(\omega)$  by the Lanczos algorithm. Here  $i$  and  $j$  are intracluster site indexes,  $l$  and  $m$  are orbital indexes. Next, we determine the full Green's function in matrix form as follows,

$$\hat{G}^{-1}(\mathbf{K}, \omega) = \hat{G}^{(c)-1}(\omega) - \hat{V}(\mathbf{K}), \quad (3)$$

where  $\mathbf{K}$  is a wave vector in the reduced Brillouin zone (the Brillouin zone of the superlattice), and  $\hat{V}(\mathbf{K})$  is the matrix of the intercluster hoppings defined as

$$\hat{V}_{il,jm}(\mathbf{K}) = \sum_h t_{il,jm}^h e^{i\mathbf{K}\mathbf{r}_h}. \quad (4)$$

Here  $\mathbf{r}_h = \mathbf{r}_g - \mathbf{r}_{g'}$ , where  $\mathbf{r}_g$  is the radius vector of the neighbor clusters labelled  $g$ .

To restore the full translation symmetry of the lattice we perform a residual Fourier transform and obtain a momentum dependent Green's function:

$$G_{lm}(\mathbf{k}, \omega) = \frac{1}{N_c} \sum_{i,j=1}^{N_c} G_{il,jm}(\mathbf{k}, \omega) e^{-i\mathbf{k}(\mathbf{r}_i - \mathbf{r}_j)}, \quad (5)$$

where  $\mathbf{r}_i$  is the radius vector of site  $i$  within the cluster,  $N_c$  is the number of sites in the cluster (which is four in our case),  $\mathbf{k}$  is a wave vector in the Brillouin zone of the initial lattice. Here we used a translational invariance of the matrix of the intercluster hoppings,  $\hat{V}(\mathbf{K}) = \hat{V}(\mathbf{k})$ .

Finally, we have Green's functions in orbital basis,  $G_{lm}(\mathbf{k}, \omega)$ .

## 2.2 Susceptibility calculation


Transverse component of the bare spin susceptibility that is a tensor in orbital indices  $l, l', m, m'$  have the following form [15],

$$\begin{aligned} \chi_{(0)}^{ll',mm'}(\mathbf{q}, i\Omega) \\ = -T \sum_{\mathbf{p}, \omega_n} G_{ml\uparrow}^{(0)}(\mathbf{p}, i\omega_n) G_{l'm'\downarrow}^{(0)}(\mathbf{p} + \mathbf{q}, i\Omega + i\omega_n). \end{aligned} \quad (6)$$

Here  $\Omega$  and  $\omega_n$  are Matsubara frequencies, and  $G_{lm\uparrow}^{(0)}(\mathbf{p}, i\omega_n)$  is the Green's function of the noninteracting system (1).

We can now make a replacement  $G_{lm\uparrow}^{(0)}(\mathbf{p}, i\omega_n) \rightarrow G_{lm\uparrow}(\mathbf{p}, \omega + i\delta)$ ,  $\delta \rightarrow +0$ , and instead of  $\chi_{(0)}^{ll',mm'}$  we will have  $\chi_{\text{cluster}}^{ll',mm'}$  with the Green's functions obtained via CPT. Thus we retain intracluster self-energy corrections but loose the long tail of intercluster effective interaction. To overcome this drawback we use RPA series with the "cluster" susceptibility  $\chi_{\text{cluster}}^{ll',mm'}$  replacing the bare electron-hole bubble, see Fig. 3. There is no double-counting problem here since the cluster susceptibility includes only self-energy corrections and RPA is the vertex renormalization.

Therefore, RPA spin susceptibility  $\chi_{+-}^{ll,mm}(\mathbf{q}, i\Omega)$  is obtained by solving the equation that is shown graphically in Fig. 3 with the interaction represented by the matrix  $U_s$  from Ref. [11]. To use matrix notations we introduce the correspondence between matrix ( $i, j$ ) and orbital indices:  $i = l + l'n_O$  and  $j = m + m'n_O$ , where  $n_O = 2$  is the number of orbitals.

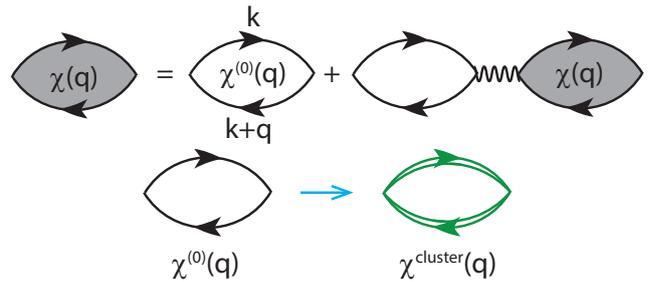

**Fig. 3** Diagrammatic representation of the RPA equation for the susceptibility  $\chi(\mathbf{q}, \omega)$  (top) and the renormalization of the Green's function forming the bare polarization bubble  $\chi_{(0)}(\mathbf{q}, \omega)$  by the CPT Green's functions (bottom). Wavy line represents two-body interaction (2).

Here we use the continuation of cluster Green's functions to Matsubara frequencies via spectral representation,

$$G_{lm}(\mathbf{k}, i\omega_n) = \int_{-\infty}^{+\infty} d\omega' \frac{A_{lm}(\mathbf{k}, \omega')}{i\omega_n - \omega'}, \quad (7)$$

where  $A_{lm}(\mathbf{k}, \omega) = -1/\pi \text{Im} G_{lm}(\mathbf{k}, \omega)$  is the spectral function.

After substituting (7) in (6) and summation over  $\omega_n$  we obtain the cluster susceptibility

$$\begin{aligned} \chi_{\text{cluster}}^{ll',mm'}(\mathbf{q}, i\Omega) = - \sum_{\mathbf{p}} \int_{-\infty}^{+\infty} \int_{-\infty}^{+\infty} d\omega' d\omega'' A_{ml}(\mathbf{p}, \omega') \times \\ \times A_{l'm'}(\mathbf{p} + \mathbf{q}, \omega'') \frac{f(\omega') - f(\omega'')}{\omega' - \omega'' + i\Omega}, \end{aligned} \quad (8)$$


where  $f(\omega) = \frac{1}{1+e^{\beta(\omega-\mu)}}$  is the Fermi function.

Physical spin susceptibility is given by the trace over orbital indices,  $\chi_{+-}(\mathbf{q}, \omega) = \frac{1}{2} \sum_{l,m} \chi_{+-}^{ll,mm}(\mathbf{q}, \omega)$ .


## 3 Numerical results

Here we present results of the numerical calculations for Hubbard repulsion  $U \leq 2$  and Hund's exchange  $J = U/4$ . Results for larger  $U$  will be published elsewhere. Plots of FS, spectral intensity for each orbital  $A_{ll}(\mathbf{k}, \omega)$ , and density of states (DOS) for two values of  $U$  are shown in Fig. 4. Spectral functions become a little broader away from the Fermi level with the increasing interaction. Apart from that the changes to the band structure and the FS are small. This is similar to the results of the variational cluster approximation (VCA) for the two-orbital model [36, 37].

Calculated spin and charge susceptibility is shown in Fig. 5. As expected, with increasing  $U$  the overall magnitude of  $\text{Re}\chi_s(\mathbf{q}, \omega)$  also increases, and the overall magnitude of  $\text{Re}\chi_c(\mathbf{q}, \omega)$  decreases.

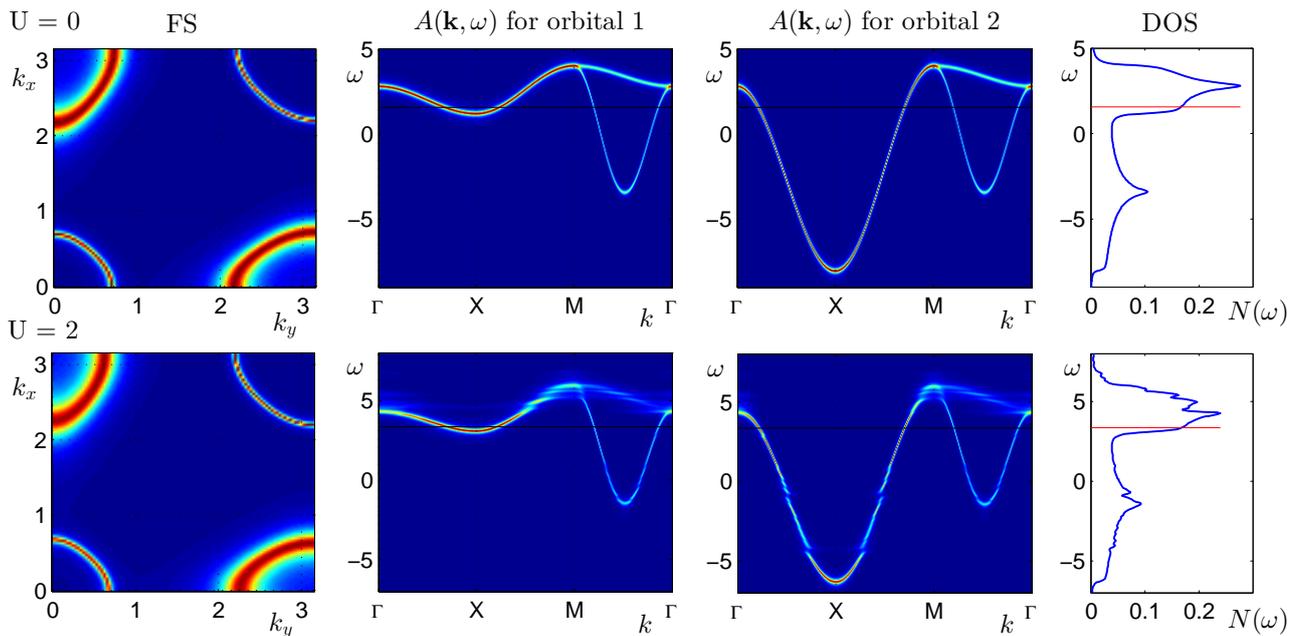

**Fig. 4** FS (on the left), spectral intensity for each orbital  $A(\mathbf{k}, \omega)$  (in the middle), and DOS (on the right) for the two-orbital model with zero and finite  $U$  are in the top and bottom row, respectively.

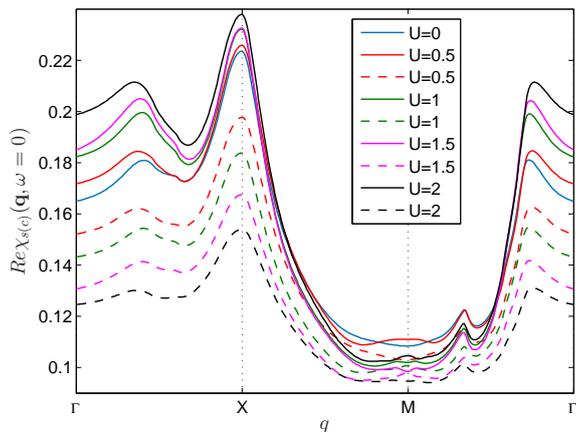

**Fig. 5** Momentum dependence of the real part of the physical spin and charge susceptibility  $\chi_{s(c)}(\mathbf{q}, \omega = 0)$  for different values of the Hubbard repulsion  $U$ . Solid line denotes the physical spin susceptibility, dashed line denotes the physical charge susceptibility.

## 4 Conclusions

We developed an approximation for calculating the spin and charge susceptibility of a multiband system with the on-site two-body interaction. It combines cluster perturbation theory for the self-energy corrections and RPA for the vertex renormalizations. Calculations for the small values of Hubbard repulsion  $U \leq 2$  revealed negligible changes in the band structure, FS, DOS, and

the spin and charge susceptibility. This essentially confirms that the rigid band approximation and the RPA for the spin and charge susceptibility are suitable approaches for the case of weak interactions.

**Acknowledgements** We acknowledge partial support by RFBR (grant 16-02-00098), RFBR and Krasnoyarsk Territory (grant 16-42-240769), and Government Support of the Leading Scientific Schools of the Russian Federation (NSh-7559.2016.2).

## References

1. Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, *J. Am. Chem. Soc.* **130**, 3296 (2008).
2. M.V. Sadovskii, *Physics-Uspekhi* **51**, 1201 (2008).
3. J. Paglione and R.L. Greene, *Nat. Phys.* **6**, 645 (2010).
4. D.C. Johnston, *Adv. Phys.* **59**, 803 (2010).
5. I.I. Mazin, *Nature (London)* **464**, 183 (2010).
6. H.H. Wen and S. Li, *Annu. Rev. Cond. Matter Phys.* **2**, 121 (2011).
7. G.R. Stewart, *Rev. Mod. Phys.* **83**, 1589 (2011).
8. P.J. Hirschfeld, M.M. Korshunov, and I.I. Mazin, *Rep. Prog. Phys.* **74**, 124508 (2011).
9. P.J. Hirschfeld, *C.R. Physique* **17**, 197 (2016).
10. I.I. Mazin, D.J. Singh, M.D. Johannes, and M.-H. Du, *Phys. Rev. Lett.* **101**, 057003 (2008).
11. S. Graser, T.A. Maier, P.J. Hirschfeld, and D.J. Scalapino, *New. J. Phys.* **11**, 025016 (2009).
12. K. Kuroki, S. Onari, R. Arita, H. Usui, Y. Tanaka, H. Kontani, and H. Aoki, *Phys. Rev. Lett.* **101**, 087004 (2008).
13. S. Maiti, M.M. Korshunov, T. A. Maier, P.J. Hirschfeld, and A.V. Chubukov, *Phys. Rev. Lett.* **107**, 147002 (2011).
14. S. Maiti, M.M. Korshunov, T.A. Maier, P.J. Hirschfeld, and A.V. Chubukov, *Phys. Rev. B* **84**, 224505 (2011).

15. M.M. Korshunov, *Physics-Uspekhi* **57**, 813 (2014).
16. H. Kontani and S. Onari, *Phys. Rev. Lett.* **104**, 157001 (2010).
17. S. Onari and H. Kontani, *Phys. Rev. Lett.* **109**, 137001 (2012).
18. A.A. Kordyuk, *Low Temperature Physics* **38**, 1119 (2012).
19. M.M. Qazilbash, J.J. Hamlin, R.E. Baumbach, L. Zhang, D.J. Singh, M.B. Maple, and D.N. Basov, *Nature Physics* **5**, 647 (2009).
20. K. Haule, J. H. Shim, and G. Kotliar, *Phys. Rev. Lett.* **100**, 226402 (2008).
21. S.L. Skornyakov et al., *Phys. Rev. B* **80**, 092501 (2009).
22. S.L. Skornyakov et al., *Phys. Rev. B* **81**, 174522 (2010).
23. Z.P. Yin, K. Haule, and G. Kotliar, *Nature Physics* **7**, 294 (2011).
24. G. Kotliar, S.Y. Savrasov, G. Palsson, and G. Biroli, *Phys. Rev. Lett.* **87**, 186401 (2001).
25. M.H. Hettler, A.N. Tahvildar-Zadeh, M. Jarrell, T. Pruschke, and H.R. Krishnaumurthy, *Phys. Rev. B* **58**, R7475 (1998).
26. A.I. Lichtenstein and M.I. Katsnelson, *Phys. Rev. B* **62**, R9283 (2000).
27. T.A. Maier, M. Jarrell, T. Pruschke, and M.H. Hettler, *Rev. Mod. Phys.* **77**, 1027 (2005).
28. D. Senechal, D. Perez, and M. Pioro-Ladriere, *PRL* **84**, 522 (2000).
29. D. Senechal, D. Perez, and D. Plouffe, *PRB* **66**, 075129 (2002).
30. S. Raghu, X.-L. Qi, C.-X. Liu, D.J. Scalapino, and S.-C. Zhang, *Phys. Rev. B* **77**, 220503(R) (2008).
31. C. Castellani, C.R. Natoli, and J. Ranninger, *Phys. Rev. B* **18**, 4945 (1978).
32. A.M. Oleś, *Phys. Rev. B* **28**, 327 (1983).
33. S.V. Nikolaev and S.G. Ovchinnikov, *JETP* **111**, 635 (2010).
34. S.G. Ovchinnikov, S.V. Nikolaev, *Pisma v ZhETP* **93**, 575 (2011).
35. S.V. Nikolaev, S.G. Ovchinnikov, *JETP* **114**, 118 (2012).
36. M. Daghofer, A. Moreo, J.A. Riera, E. Arrigoni, D.J. Scalapino, and E. Dagotto, *Phys. Rev. Lett.* **101**, 237004 (2008).
37. R. Yu, K.T. Trinh, A. Moreo, M. Daghofer, J.A. Riera, S. Haas, and E. Dagotto, *Phys. Rev. B* **79**, 104510 (2009).